

NI 43-101 TECHNICAL REPORT



LITHIUM INFERRED MINERAL RESOURCE ESTIMATE
CLAYTON VALLEY
ESMERALDA COUNTY, NEVADA
USA

Prepared for

Noram Ventures, Inc. and Alba Minerals Ltd.

Effective Date: July 24, 2017

Qualified Person: Bradley C. Peek, MSc., CPG
Qualified Person: Raymond P. Spanjers, MSc, RPG

Contents

List of Figures	ii
List of Tables	iii
1 Summary	1
2 Introduction.....	2
Abbreviations and Acronyms Used in Report	3
3 Reliance on Other Experts	4
4 Property Description and Location	4
5 Accessibility, Climate, Local Resources, Infrastructure and Physiography	8
6 History.....	9
7 Geologic Setting and Mineralization	10
7.1 Geology – Spartan Claims	13
7.2 Geology – Zeus Claims.....	13
7.3 Mineralization	14
8 Deposit Types	17
9 Exploration.....	17
9.1 Surface Sampling Method and Approach.....	18
10 Drilling.....	19
11 Sample Preparation, Analyses and Security	25
12 Data Verification.....	31
13 Mineral Processing and Metallurgical Testing	32
13.1 Li vs. Ca Correlation.....	33
14 Mineral Resource Estimates	35
14.1 General.....	35
14.2 Economic Factors.....	36
14.3 Lithium Pricing	38
14.4 Cut-off Grade	40
14.5 Model Parameters	40
14.6 Density Determination	50
14.7 Model Results	51

23 Adjacent Properties	54
24 Other Relevant Data and Information.....	55
25 Interpretation and Conclusions	55
25 Recommendations.....	56
26 References.....	57
Certificate of the Author	59
Date and Signature Page.....	60
Consent of Qualified Person:	63

List of Figures

Figure 1 – Property location map.....	6
Figure 2 – Overview of Noram Ventures’ claims in the Clayton Valley and their spatial relationship to Albemarle’s evaporation pond operations at Silver Peak (See also Fig 5).....	7
Figure 3 – Daily high and low temperatures for Tonopah, Nevada.....	9
Figure 4 – Physiographic features surrounding Clayton Valley, Nevada.....	10
Figure 5 – Generalized geologic map from Zampirro (2005) with Noram Ventures’ claim outlines (blue stippled areas) added.....	12
Figure 6 – Example of the ridges and washes encountered on the Zeus claim group.....	14
Figure 7 – Schematic deposit model for lithium brines (Bradley, 2013).....	15
Figure 8 – Example of gypsum (?) blebs in a tuffaceous, calcareous mudstone.....	16
Figure 9 – Example of algal mats in the Esmeralda Formation on the Zeus claims.....	16
Figure 10 – Digitate algal structures in the Esmeralda Formation on the Zeus claims.....	17
Figure 11 - Locations of the 46 sites drilled during the Phase 1 drilling campaign.....	20
Figure 12 - Enlarged map of collar locations of the 44 core holes drilled on the Zeus claims.....	23
Figure 13 - Shaw Tools backpack core drill in operation on the Zeus claims.....	24
Figure 14 – Geologist Michael Keller in box trailer used for core logging and sampling.....	26
Figure 15 - Sealed shipping containers, before and after applying duct tape.....	27
Figure 16 - Range of values for MEG-Li.10.13.....	28
Figure 17 - Range of values for MEG-Li.10.14.....	29
Figure 18 - Distribution of Blank Standard results.....	30
Figure 19 - Comparison of duplicate sample pairs.....	31
Figure 20 - Graph of Li (ppm) vs. Ca + Mg(%).....	34
Figure 21 - China "Spot" prices from Lithium Americas Corp. 2017 AGM presentation.....	39
Figure 22 - Histogram of all Li values from close-spaced drill holes.....	41
Figure 23 - Polygon used to constrain model horizontally.....	44
Figure 24 - Profiles A1-A3 through inverse distance model. Vertical exaggeration = 5X.....	45
Figure 25 - Profiles A4-A6 through inverse distance model. Vertical exaggeration = 5X.....	46
Figure 26 - Profiles A7-A9 through inverse distance model. Vertical exaggeration = 5X.....	47

Figure 27 - Locations of Profiles A1-A9.	48
Figure 28 – Fence diagram through the inverse distance model.	49
Figure 29 - Relationship between specific gravity and lithium values.	51

List of Tables

Table 1 - Claims with BLM NMC numbers.	5
Table 2 - QA/QC samples used for the Phase 1 drilling.	27
Table 3 - Comparison summary of Close-Spaced Holes to Total Drilling Program	35
Table 4 - Estimated costs to produce one tonne of lithium carbonate.	37
Table 5 - Statistics for all Li values from close-spaced drill holes.	42
Table 6 - SG sample statistics.	50
Table 7 - Inverse distance calculated values for each level and Li (ppm) grade range.	53
Table 8 - Inferred Mineral Resource final numbers.	54
Table 9 – Recommended 2 nd Phase – Drilling budget.	56

1 Summary

This Technical Report is prepared for Noram Ventures, Inc. (Noram) and Alba Minerals Ltd (Alba). Both are publicly traded Canadian corporations with corporate offices in Vancouver, BC, Canada. Both companies are listed on the TSX Venture Exchange (Noram's symbol is TSX-V:NRM; Alba's symbol is TSX-V:AA-H). Alba has entered into an option agreement with Noram and its wholly-owned subsidiary, Green Energy Resources (Green Energy) to purchase a 25% interest, with an option to acquire a further 25% interest, in the properties (also herein called the "claims") described in this report.

Noram acquired a land position in the Clayton Valley of Nevada consisting of 888 placer claims. The land package covers 17,738 acres (7,178 hectares). The perimeter of Noram's claims are located within 1 mile (1.6 kilometers) of Albemarle Corporation's (Albemarle's) lithium brine operations. Lithium is produced at Albemarle's plant from deep wells that pump brines from the basin beneath the Clayton Valley playa. The plant is the only lithium producer in the United States and has been producing lithium at this location continuously since 1967.

Between Albemarle's operation and Noram's land position lies Pure Energy Minerals' Clayton Valley South project where Pure Energy has announced an NI 43-101 compliant inferred resource of 218,000 metric tonnes of lithium carbonate equivalent (LCE) above a cutoff of 20 mg/l (Blois et al, 2017). This resource occurs as basinal brines like those at Albemarle's project. The resource has not been verified by the author, and is not necessarily indicative of the mineralization that is the subject of this technical report.

Noram's drilling of 46 shallow core holes into the lithium-rich sediments that were previously identified through surface sampling has provided a basis for the definition of an inferred lithium resource. The lithium assays from the drilling provided results that were quite consistent over a reasonably large area of close-spaced drill holes. The model generated for the inferred resource estimate indicated a zone of higher lithium grades trending northwest-southeast through the area of the resource, perhaps reflecting an ancient shoreline of the playa lake bed. The model that was generated from the close-spaced drilling was very homogeneous. The deposit remains open in all directions and at depth and the drilling tested less than 1% of the area covered by the extensive claim holdings. There is considerable upside potential for increasing the size of the deposit. However, such potential is conceptual in nature. There has been insufficient exploration beyond the modeled deposit and it is uncertain if further exploration will result in an enlargement of the deposit.

The model herein reports an Inferred Mineral Resource of approximately 17 million metric tonnes at a grade of about 1060 ppm Li, which equates to 96,476 LCEs. The level of confidence, i.e., the category, of a resource estimate may change with additional exploratory work, such as sampling, drilling, etc.

One of the keys to the project is to determine if lithium can be economically extracted from the sediments. To this end Noram commissioned Membrane Development Specialists LLC (MDS)

to investigate the amenability of the subject property's sediments to lithium extraction using new membrane processes. Their findings, and a recent report by AuTec (Baron, 2017) summarizing and explaining the MDS work, although preliminary in nature, have shown that the test materials were amenable to an acid leach, ultrafiltration, nanofiltration and reverse osmosis process to separate the lithium from the test material and remove a large portion of the magnesium and calcium with no rejection of lithium. MDS and AuTec were able to supply some initial estimates of the costs to process the sample material to recover a metric tonne of lithium carbonate. The MDS estimate for operating costs was US\$2,045 per short ton (US\$2,255 per metric tonne) of lithium carbonate. When combined with other operating costs, these analyses indicate that the cost to produce a tonne of lithium carbonate will be approximately US\$ 3,750/tonne for the average grade of the deposit. With the current price for lithium carbonate in the range of US\$ 14,000 to US\$ 15,500 per tonne (Lithium Miner News for the Month of July 2017), it serves to show that there is a reasonable chance that the deposit could be economically exploited. It also shows that even the lowest lithium grade used in the Inferred Resource model (454 ppm Li) may be economically viable to mine at current lithium carbonate prices and that all of the resource within the model may be economically recoverable.

This report recommends a second phase of shallow core drilling, requiring a budget estimated to be US \$90,000, and a concurrent pilot-scale test by MDS to further demonstrate the extractability of lithium from the clays, the latter program having a budget estimated at US \$480,000.

2 Introduction

This Technical Report is prepared for Noram Ventures, Inc. (Noram) and Alba Minerals Ltd (Alba). Both are publicly traded Canadian corporations with corporate offices in Vancouver, BC, Canada. Both companies are listed on the TSX Venture Exchange (Noram's symbol is TSX-V:NRM; Alba's symbol is TSX-V:AA-H). Alba has entered into an agreement with Noram and Green Energy to acquire interests in the properties described in this report. The acquisition terms are described in Section 4 below.

The property has been the subject of two previous Technical Reports, one for Noram dated October 24, 2016 and one for Alba dated January 13, 2017.

The majority of information contained in this report was generated by the author during and in conjunction with trips to the properties. Other information was gleaned from various sources and, when possible, verified by the author. These other sources being:

- Published literature
- Noramventures.com website
- Albamineralsltd.com website
- U. S. Bureau of Land Management LR2000 website for verification of claim status
- Membrane Development Specialists (MDS) provided two confidential reports dealing with the lithium extraction process testing and estimates of related processing costs (Section 13).

- AuTec Innovative Extractive Solutions Ltd. (AuTec) provided a review of the MDS process with comments and explanations of the MDS findings.

Sources are also referenced in the text of this document, where appropriate.

The author has made five trips to the property that is the subject of this report. The property visits were on the following dates:

- May 5 – 7, 2016 (Surface Phase 1)
- July 21 – 25, 2016 (Surface Phase 2)
- August 3 – 6, 2016 (Surface Phase 3)
- December 12 – 22, 2016 (Drilling)
- January 8 – 27, 2017 (Drilling)

During the visits the author supervised core drilling, collected samples for assay, noted some aspects of the geology, took photographs and, on a rare occasion, assisted with the claim staking. These activities were conducted in conjunction with Harrison Land Services, who was under contract with Noram and Noram's wholly owned subsidiary, Green Energy Resources, to stake claims, to collect samples and geologic information and to test a portion of the property by core drilling.

Abbreviations and Acronyms Used in Report

ATV	All-Terrain Vehicle
BLM	U. S. Bureau of Land Management
Ca	Chemical symbol for calcium
LCE	Lithium Carbonate Equivalent (Li_2CO_3)
Li	Chemical symbol for lithium
Mg	Chemical symbol for magnesium
MDS	Membrane Development Specialists LLC
NSR	Net smelter return royalty
NV	Nevada
PPM	Parts per million
RQD	Rock quality designation
SG	Specific Gravity

3 Reliance on Other Experts

Co-author Raymond P. Spanjers, MSc, RPG is responsible for Section 14 – Mineral Resource Estimates.

Gavin Harrison of Harrison Land Services, who is not a Qualified Person, supplied most of the information regarding the staking and locations of the placer mining claims. Mr. Harrison has more than 10 years of experience staking and recording claims on BLM land in several states in the western U. S. Co-author Brad Peek verified the presence and location of many of the claim stakes and location documents on the ground and for some of the claims, witnessed the recording of claims at the Esmeralda County Courthouse in Goldfield, Nevada. Harrison Land Services was also responsible for production of the claim location map used in this report.

Star Point Enterprises, Inc. was responsible for a scoping study of the water rights situation in the Clayton Valley, Nevada (Section 24).

All other sections of the report are the sole responsibility of co-author Bradley C. Peek, MSc., CPG.

4 Property Description and Location

The properties are located in Esmeralda County, Nevada approximately halfway between Las Vegas and Reno (Figure 1). The property position consists of a total of 888 placer claims covering 17,760 acres 212(7,193 hectares) staked on U. S. Government land administered by the U. S. Bureau of Land Management (BLM). Each claim covers an area of 20 acres (8.1 hectares). The claims are in two non-contiguous groups. The northern group has been named the Li Group and consists of 188 placer claims staked in portions of Townships T1S, R39E and T1S, R40E, Mt. Diablo Principal Meridian. The southeasterly group consists of the Zeus, Zeus XT, Hades and Spartan claims, which are contiguous with each other. This southeastern group is made up of 700 placer claims and is located in portions of townships T2S, R40E; T2S, R40 1/2E and T3S, R40E, Mt. Diablo Principal Meridian (Figure 2). All claim corners and location monuments were located using handheld Gamin GPS units (Gavin Harrison, personal communication, and in part, witnessed by the author).

The initial claims, the Li group, were staked by Harrison Land Services acting as a contractor for Stadnyk and Partners USA Corp. and were subsequently acquired by Noram through purchase (Noramventures.com news releases dated April 25 and April 27, 2016). Stadnyk and Partners retained a 2.5% NSR royalty from this transaction. Later claim acquisitions were accomplished through claim staking by wholly owned subsidiary Green Energy Resources using Harrison Land Services as the claim staking contractor (Gavin Harrison, personal communication) (Noramventures.com news releases dated May 26, June 7 and June 29, 2016). The 50 Spartan claims that were previously held in trust by Plateau Ventures LLC were transferred to Green Energy Resources and the Quit Claim Deed was recorded with Esmeralda County in January 2017 (Gavin Harrison, personal communication). All 888 claims are owned 100% by Noram,

beneficially through Green Energy. Table 1 is a listing of all of the claim names and BLM NMC numbers for the claims that have been assigned numbers.

All 888 claims are located on unencumbered public land managed by the federal Bureau of Land Management (BLM). Annual holding costs for the claims are \$155 per claim per year to the BLM, due August 31st. There is also a \$4 per claim annual document fee to be paid to Esmeralda County each year, due November 1st. There is no set expiration of the claims as long as these payments are made annually.

There are no known significant factors or risks that may affect access, title or the right or ability to perform work on the Noram claim areas.

Table 1 - Claims with BLM NMC numbers.

Claim No.	Claim No.	BLM No.	BLM No.
From	To	From	To
LI-001	LI-188	NMC1125249	NMC1125436
Zeus-001	Zeus-150	NMC1126587	NMC1126736
Zeus XT-001	Zeus XT-150	NMC1134326	NMC1134473
Spartan-001	Spartan-050	NMC1125697	NMC1125746
Hades-001	Hadies-75	NMC1134151	NMC1134225
Hades-076	Hades-101	NMC1128495	NMC1128520
Hades-102	Hades-145	NMC1134226	NMC1134266
Hades-146	Hades-172	NMC1128521	NMC1128547
Hades-174	Hades-174	NMC1128548	NMC1128548
Hades-175	Hades-223	NMC1134268	NMC1134317
Hades-224	Hades-260	NMC1128549	NMC1128585
Hades-261	Hades-267	NMC1134318	NMC1134324
Hades-268	Hades-301	NMC1128586	NMC1128619
Hades-303	Hades-303	NMC1134325	NMC1134325
Hades-304	Hades-350	NMC1128620	NMC1128666

In an agreement dated December 20, 2016 with Green Energy and Noram, Alba purchased a 25% interest in the claims for CDN\$255,000 and received an option to acquire up to an additional 25% interest in the claims, all subject to the 2.5% NSR. To acquire the full 50% Alba must pay Green Energy a further CDN\$845,000 by a series of installments over the period ending November 30, 2017 and issue 1,000,000 common voting shares in its capital to Noram on or before November 30, 2017 (Noramventures.com press release dated February 22, 2017).

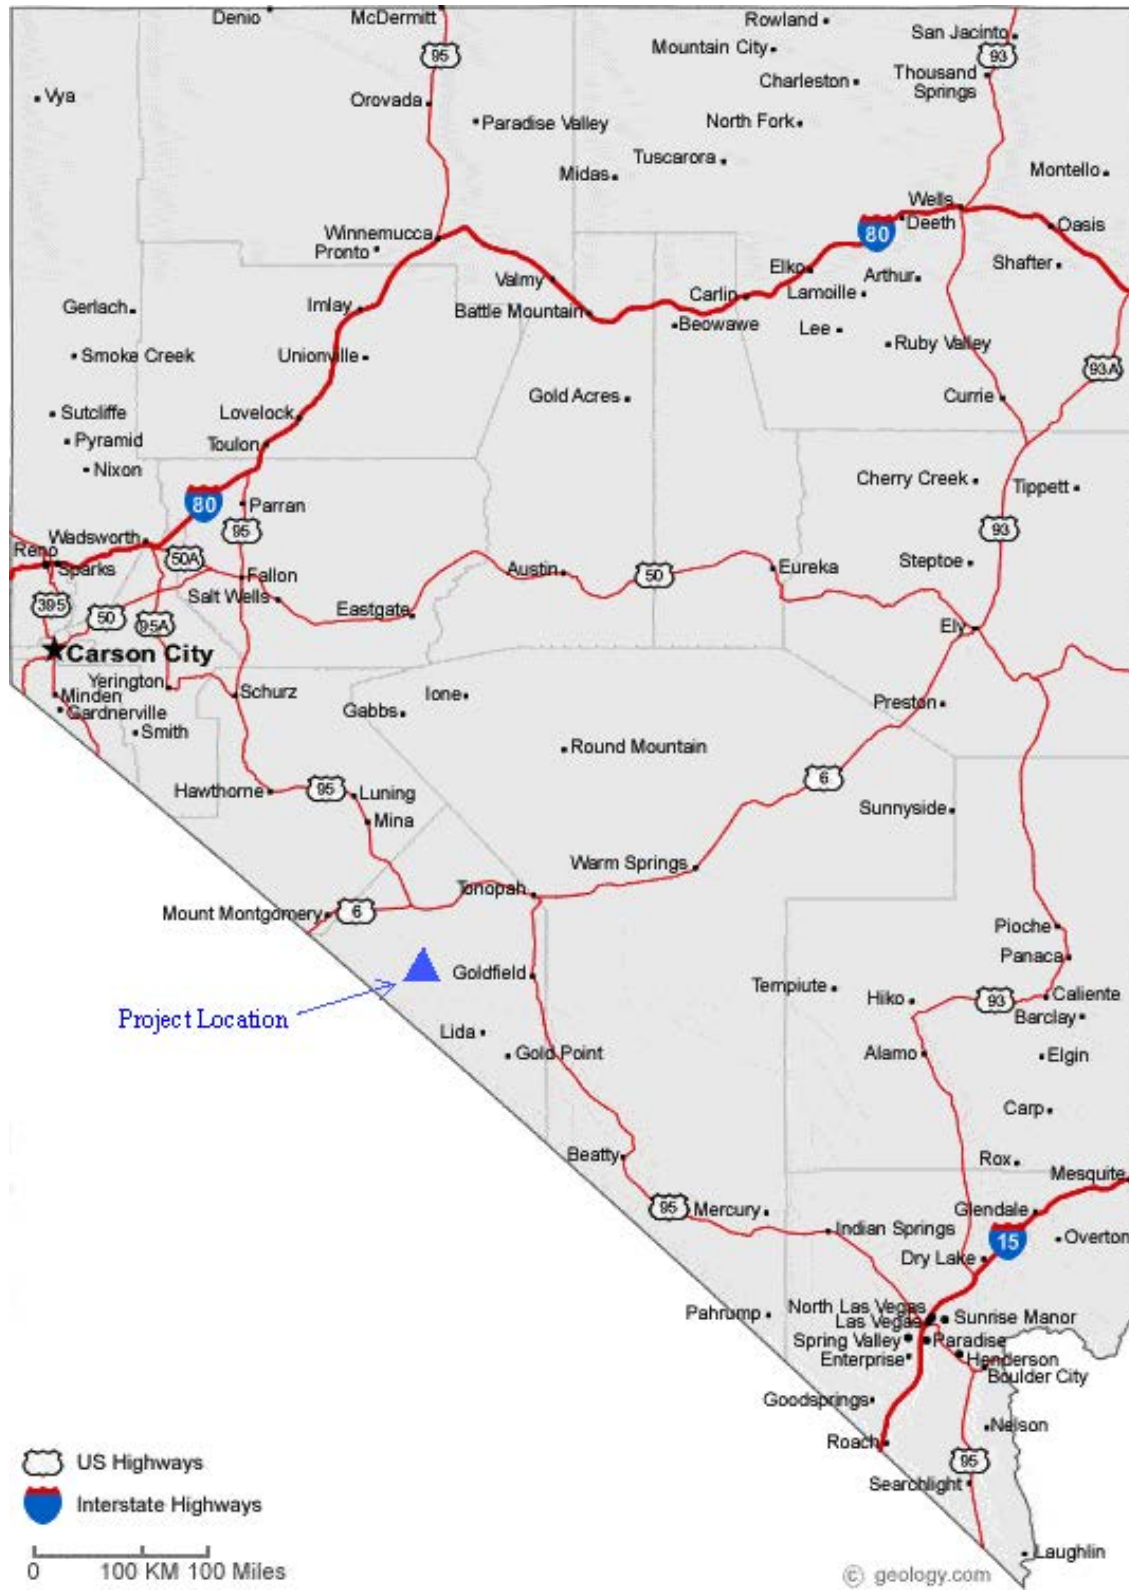


Figure 1 – Property location map.

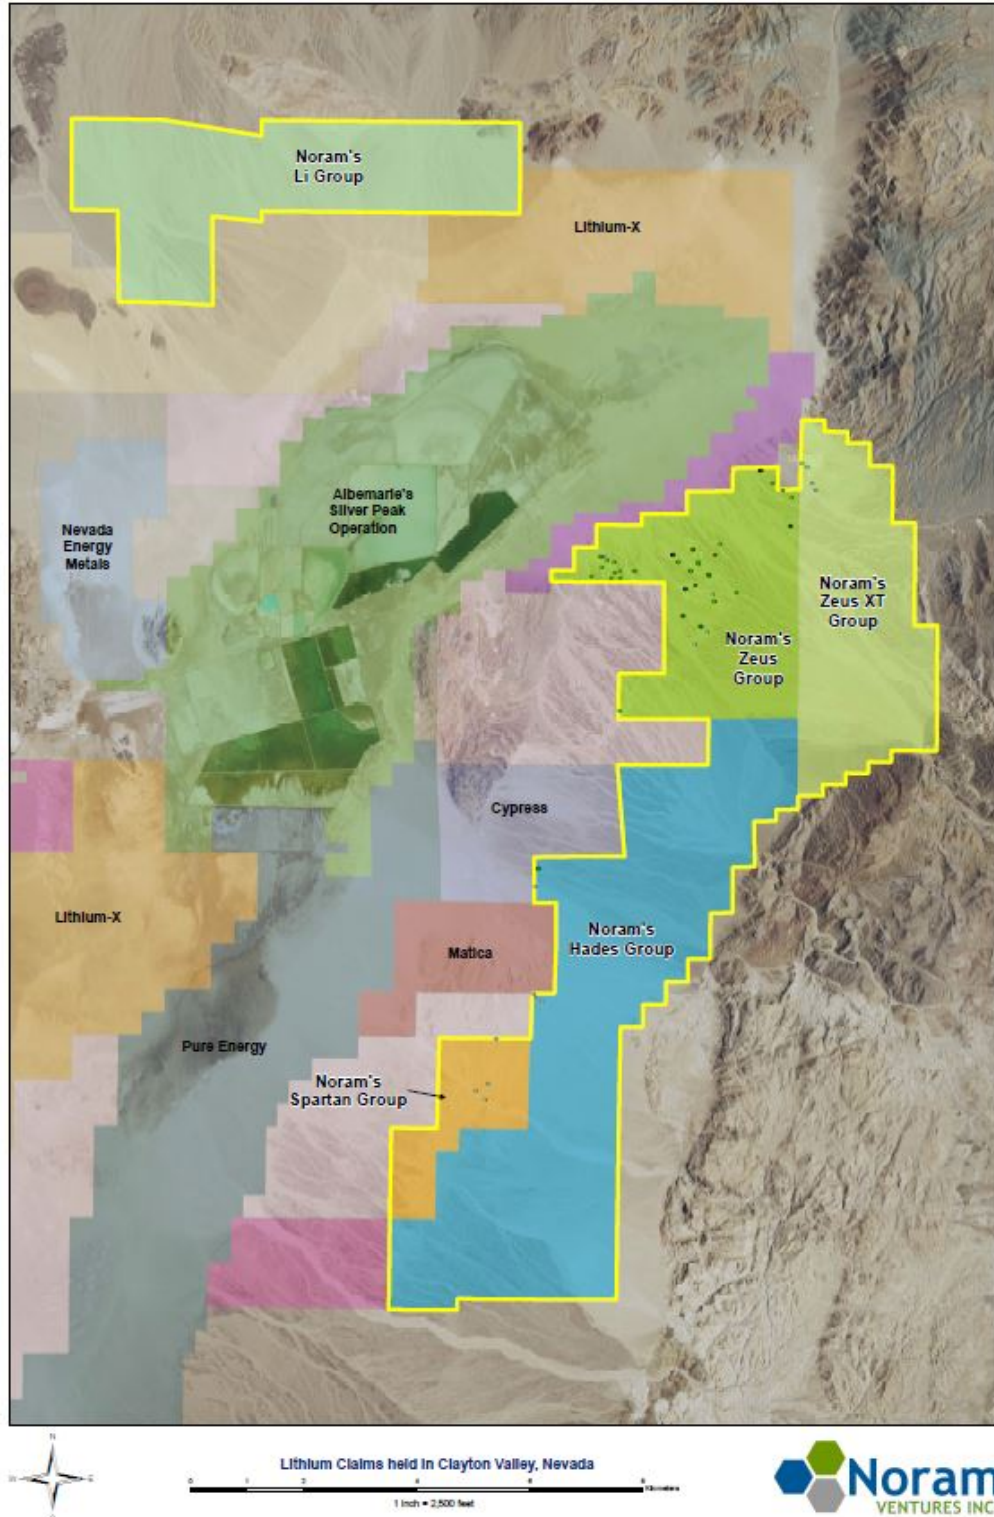


Figure 2 – Overview of Noram Ventures' claims in the Clayton Valley and their spatial relationship to Albemarle's evaporation pond operations at Silver Peak (See also Fig 5).

To the author's knowledge the land under claim contains no buildings or other structures. There are no known mineralized zones on the surface of Noram's staked land, other than those defined by the drilling described in this report and the surface sampling described in previous Technical Reports. To the author's knowledge there are no environmental liabilities associated with the property position, nor any mine workings or development of any sort, excepting the shaft discussed in previous Noram and Alba Technical Reports.

An Exploration Plan of Operations to drill 55 core holes was submitted on behalf of Green Energy Resources to the Tonopah, Nevada office of the Bureau of Land Management (BLM). The BLM in Nevada works in conjunction with the Nevada Bureau of Mines and Geology for the permitting processes on public lands. Since the surface disturbance for the drilling was to be held to less than 5 acres (2.02 hectares), only a Notice of Intent was required. The BLM responded with a Decision that a Bond of US\$ 7,092.00 would be required prior to commencement of operations. The Bond was submitted and accepted in early December 2016 and drilling began on December 13, 2016.

5 Accessibility, Climate, Local Resources, Infrastructure and Physiography

Generally speaking, all the Noram claims fall between elevations of 4300 and 5200 feet above sea level. The topography is mostly gently sloping basin margins consisting of unconsolidated sediments. These sediments are cut by typical desert washes, which can be steep sided. The area can mostly be traversed by 4-wheel drive vehicles, but often with some difficulty. There are few roads crossing the property.

The vegetation of the region is sparse, mostly consisting of widely spaced low brush. No trees are present. The area lies in the eastern rain shadow of the Sierra Nevada and is high desert. Tonopah, the nearest town of any size has average annual precipitation of 5.14 inches (130.6 mm). In July, the hottest month, it has an average high temperature of 91.9°F (33.3°C) and an average low temperature of 57.5°F (14.2°C). In December, the coldest month, it has an average high temperature of 44.3°F (6.8°C) and an average low of 19.4°F (-7°C) (Source: Wikipedia.com). Figure 3 below is a graphic representation of the Tonopah average temperatures (Source: Weatherspark.com).

The mild climatic conditions allow for field work to continue throughout the year, however drilling was temporarily limited in winter by the problem of freezing water lines.

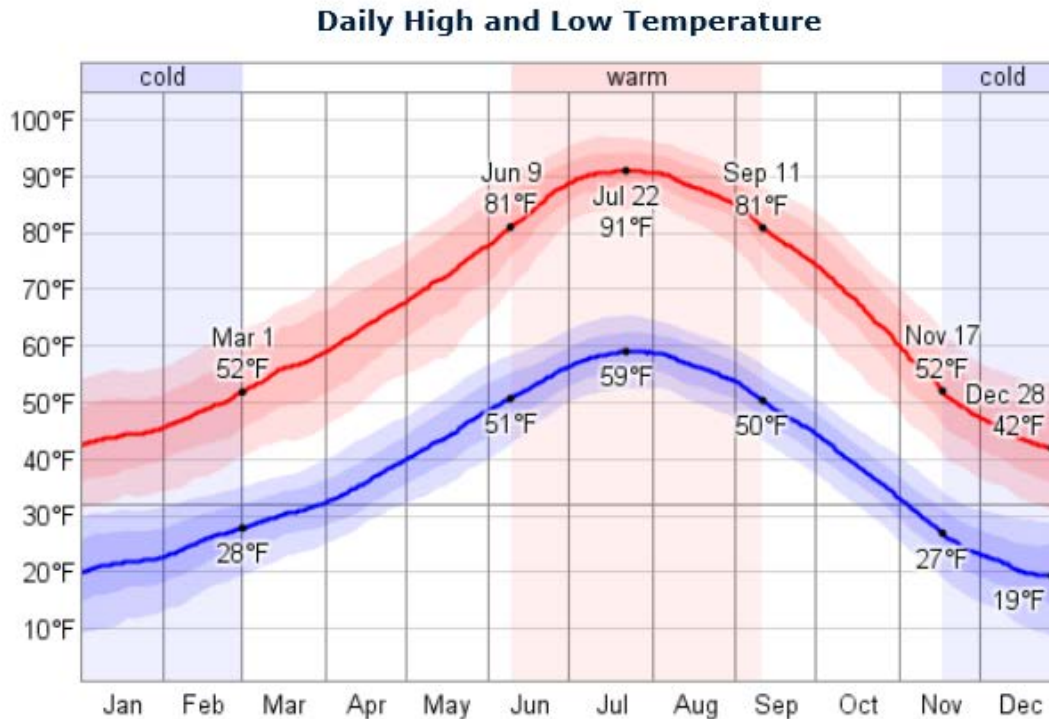


Figure 3 – Daily high and low temperatures for Tonopah, Nevada.

The property can be accessed from Tonopah by driving south on U. S. Highway 95 for a distance of 7 miles (11 kilometers) and then southwest on the Silver Peak gravel road for a distance of 20 miles (32 kilometers). Both of these roads underwent upgrades during the summer of 2016. It is now possible to drive to the edge of the property entirely on paved roads by driving south 21 miles (34 km) on Highway 95 and then driving 11 miles west on the newly paved Silver Peak Road.

6 History

The Albemarle Corporation operations at Silver Peak, Nevada, within the Clayton Valley, is the site of the only lithium production in North America. Brines containing lithium are pumped from wells that penetrate the playa sediments. The brines are concentrated through a series of evaporation ponds and the resulting salts are processed to extract lithium at the plant at Silver Peak.

Following the lithium price rise in recent years, several exploration companies became interested in the Clayton Valley resulting in several thousand new claims being staked, surrounding the Albemarle land holdings. In early 2016 Harrison Land Services became aware of some unstaked land in close proximity to the Albemarle land holdings. Harrison Land Services was put in touch with Noram Ventures, who eventually funded the staking program for their initial claim position, the Spartan and Li claim groups. Market response to the acquisition and initial exploration successes have provided the impetus to stake the additional claims that Noram now holds.

The claims that comprise the properties have been staked on U. S. Government land that was open to staking. There have been no previous owners, previous mineral resource or reserve estimates and no previous production from the properties.

7 Geologic Setting and Mineralization

The Clayton Valley is a closed basin playa surrounded by mountains. Figure 4 (from Davis and Vine, 1979) shows the physiographic features in the Clayton Valley area.

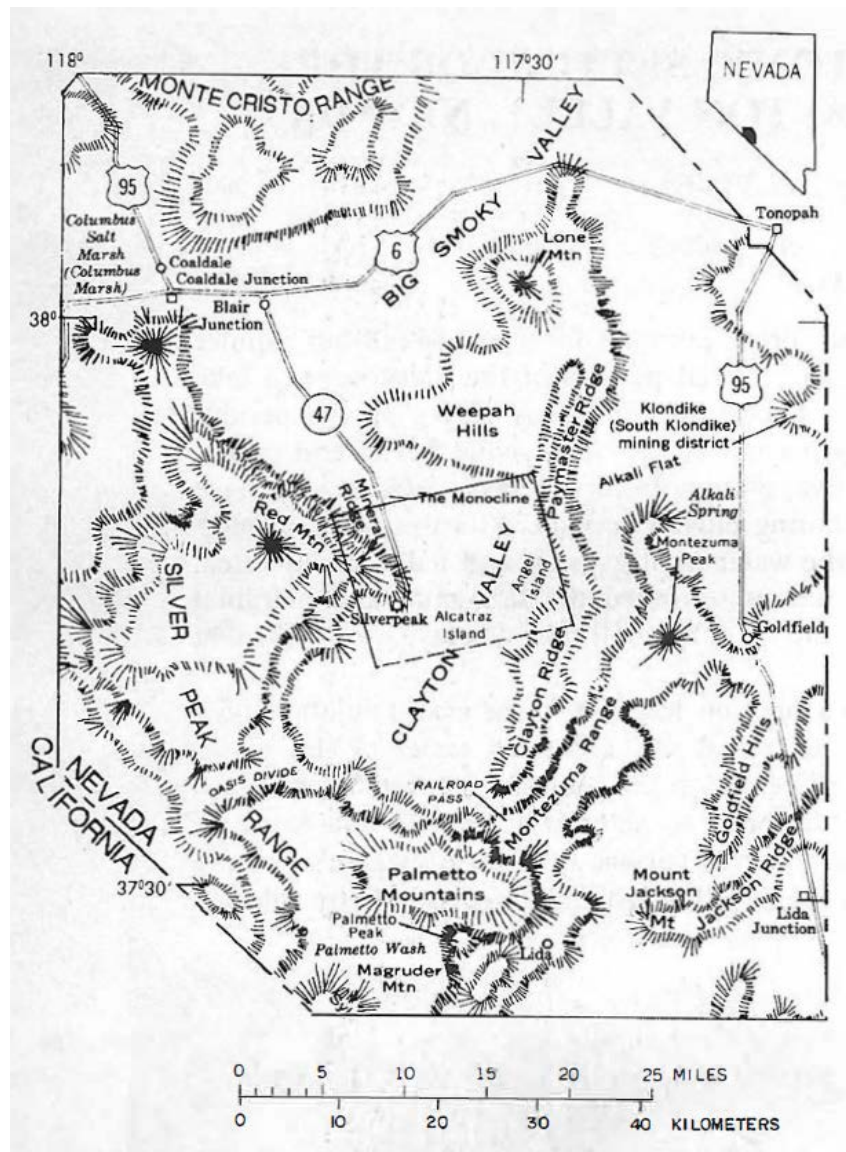


Figure 4 – Physiographic features surrounding Clayton Valley, Nevada.

Clayton Valley is flanked on the north by the Weepah Hills, on the east by Clayton and Paymaster Ridges and on the west and south by the Silver Peak Range and the Palmetto Mountains. The playa floor is approximately 40 square miles (100 square kilometers). Altitudes

range from 4,265 feet (1300 meters) on the playa floor to 9,450 feet (2,880 meters) at Piper Peak (Davis and Vine, 1979).

Tectonically, the Clayton Valley occurs in the Basin and Range Province. Figure 5, from Zampirro (2005) is a generalized geologic map of the Clayton Valley area with the Noram land position superimposed. The province is dominated by horst and graben faulting and some right lateral motion since Tertiary time, which continues to the present (Foy, 2011). The basement is made up of Neoproterozoic to Ordovician carbonate and clastic rocks that were deposited along the ancient western passive margin of North America. The basin is bounded to the east by a steep normal fault system toward which basin strata thicken (Munk, 2011). Structural and stratigraphic controls have divided the basin into six economic, yet potentially interconnected, aquifer systems (Zampirro, 2005). The sediments deposited in the basin are primarily silt, sand and gravel interbedded with illite, smectite and kaolinite clays (Kunasz, 1970 and Zampirro, 2005). These sediments include a substantial component of volcanoclastics. Green and tan tuffaceous claystones and mudstones on the eastern margin and above the playa sediments, best described by Davis (1981), have thus far been the primary objective of Noram's exploration effort and are considered by Kunasz (1979) and Munk (2011) to be the primary source of the lithium for the basin brines.

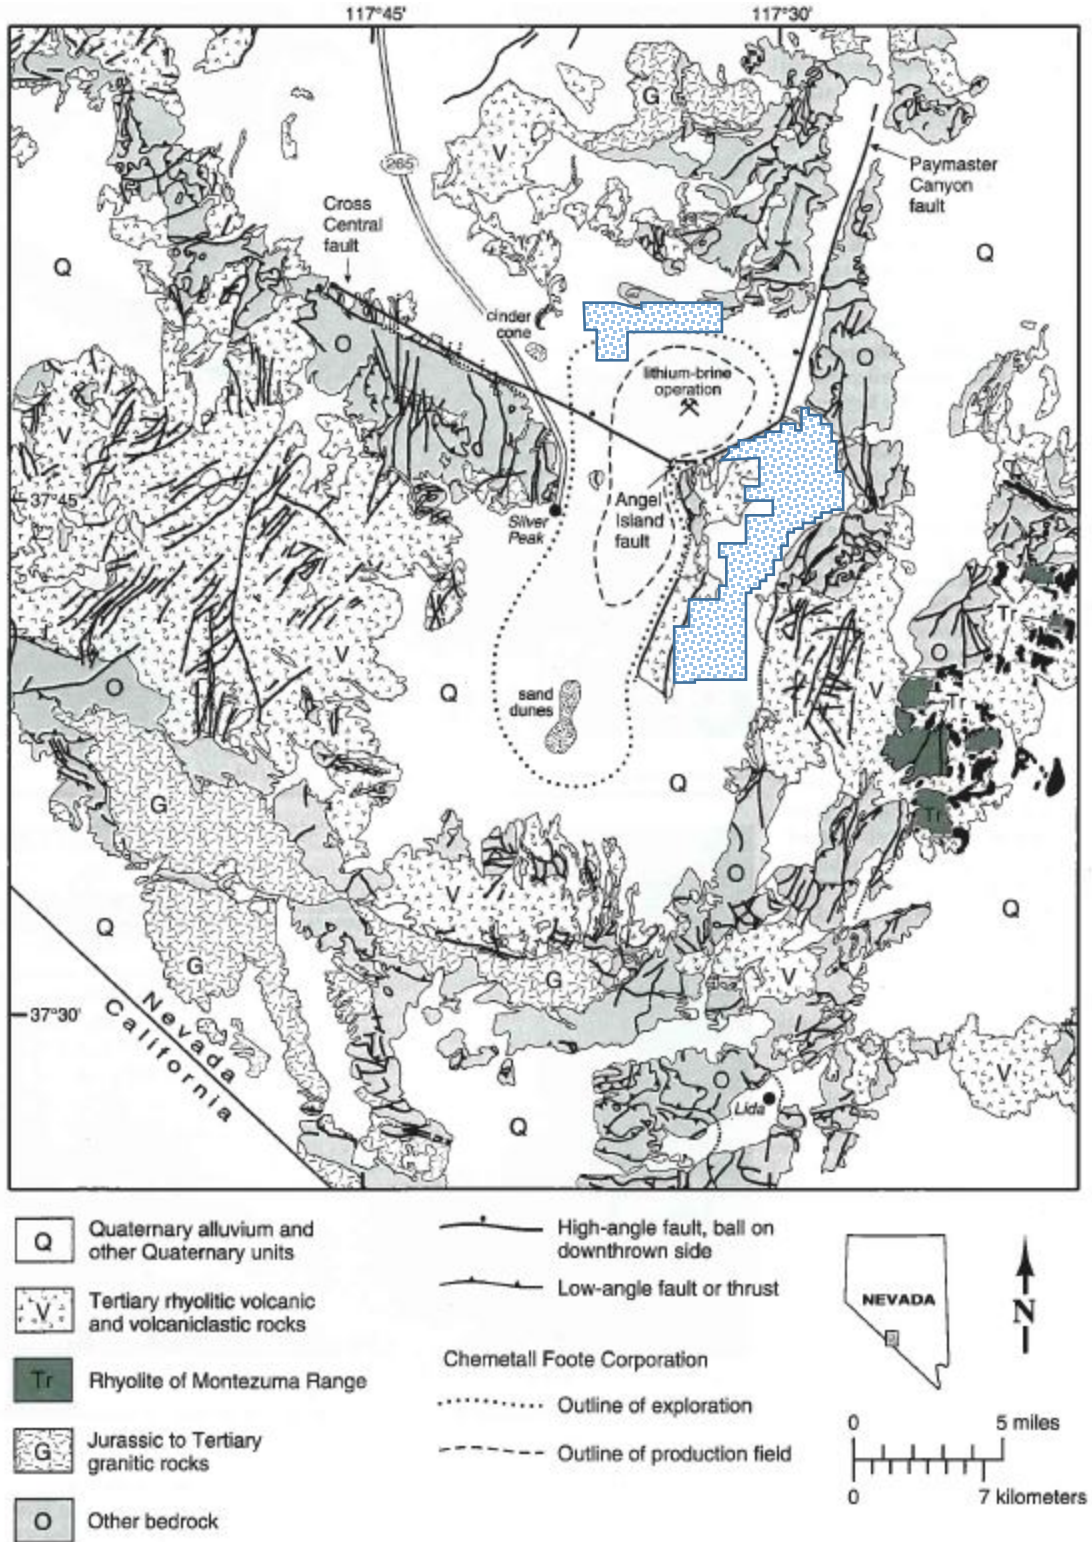


Figure 5 – Generalized geologic map from Zampirro (2005) with Noram Ventures’ claim outlines (blue stippled areas) added.

During the visits to the Noram properties the only areas where the geology was investigated has been on portions of the Zeus, Zeus XT, Hades and Spartan claim groups. No actual geologic mapping was undertaken during these visits, but the following geologic information was noted. The Li claim group was not investigated by the author.

7.1 Geology – Spartan Claims

The area of the Spartan claims is southeast of the Rockwood (now Albemarle) lithium mine. It is an area of small mesas capped by more resistant sandy limestones and limey sandstones. Tan and green clay units are present on the slopes of many of the washes that cut through the claim block. The Geology and Mineral Deposits of Esmeralda County (Albers & Stewart, 1972) has classified these rocks as Tertiary age Esmeralda Formation. Their description of the Esmeralda is “Bedded tuff and tuffaceous sedimentary rocks”, which matches the lithologies observed in the field. A few thick (up to 10 feet (3 meters)) units, which appear to be a totally unconsolidated ash-fall tuff, were observed.

7.2 Geology – Zeus Claims

The Zeus claim block, which was the primary focus of the Phase 1 drilling, covers a large area that gently slopes toward the northwest. The drainages, or washes, cut through the Tertiary Esmeralda Formation. The Esmeralda in this area is made up of fine grained sedimentary and tuffaceous units which generally dip to the northwest, but while the strike and dip can be quite varied in some portions of the claims, most of the sediments dip at less than 5°. Some bedding undulations were noted, possibly caused by differential compaction. Faulting was also noted in some zones, mostly in the northwestern regions of the claims, but due to time constraints, the faults have not been traced.

The resulting topographic configuration consists of long rounded “ridges” of Esmeralda Formation separated by gravel filled washes. The ridges were generally 50’ (15m) to 100’ (30m) wide and had lengths of a few hundred to a few thousand feet and trended northwest. These geomorphic features have been described by some authors (Davis, 1981; Kunasz, 1974) as a “badlands” type topography. The depth of the Esmeralda Formation was not determined by the author, since the base of the formation was not seen in any of the washes. Davis (1981) measures this section at approximately 100 meters (328 feet) thick and Kunasz (1974) described it as being approximately 350 feet (107 m) thick. In some areas it was noted by the author to be in excess of 100 feet (30 m) thick where washes cut through the thicker exposures. The ridges are topped with weathered remnants of rock washed down from the surrounding mountainous areas; a weathering phenomenon typical of the desert terranes. The photo below is an example of such topography.



Figure 6 – Example of the ridges and washes encountered on the Zeus claim group.

The Esmeralda Formation in the main area of interest on the Zeus claims was mostly soft and crumbly siltstones, mudstones and claystones, but contained several thin beds of harder, more consolidated sediments. Most beds were tuffaceous, as evidenced by fine crystal shards. Nearly all of the sediments are calcareous, indicating lakebed deposition. Several of the samples contained vugs or voids partially filled with a white soft evaporite (?) mineral, probably gypsum (Figure 8). A further indication of lakebed sedimentation is evidenced by algal mats (Figure 9) and digitate algal features (Figure 10).

7.3 Mineralization

The brine mineralization within the Clayton Valley has been documented by numerous studies spanning several decades. Brine targets have not yet been investigated on Noram's claims.

The targeted mineralization investigated by Noram occurs at surface in the form of sedimentary layers enhanced in lithium to the extent that the lithium appears to be extractable from them economically, although this has not yet been demonstrated through in-depth economic analysis. The relationship of these targeted lithium-bearing sedimentary layers with respect to brine-related Li-extraction evaporation ponds is illustrated schematically in Figure 7. Noram's claim locations with respect to an existing evaporation-pond Li recovery operation is shown in Figure 2 above. The targeted layers occur primarily as light green, interbedded tuffaceous mudstones and claystones. The beds are nearly always calcareous and most often salty. The mudstones are usually poorly consolidated, while the thin claystone beds can be well consolidated and often form nodules. Occasionally there are sandy beds, as well. The units occur as lakebed sediments that have been mapped (Albers and Stewart, 1972; Davis, 1981) as Miocene or Pliocene

Esmeralda Formation. Algal mats and even digitate algal features have been noted on occasion, but these are generally not well preserved. The beds are gently dipping, usually to the northwest, but with local undulations. These units have been shown by Kunasz (1970) to be the probable source of lithium for the basin brines. Exploration for this mineralization, which confirmed the existence of anomalously high levels of lithium within sediments on Noram’s claims is documented in Section 9 below. The deposit that is the subject of this report is part of a section of ancient lakebed sediments that were raised above the current Clayton Valley playa by Basin and Range faulting, which is present throughout the region.

Lengths, widths, depths and continuity of the mineralization are not yet known, and are currently being determined by Noram. This report includes recommendations and a budget for continuing this work.

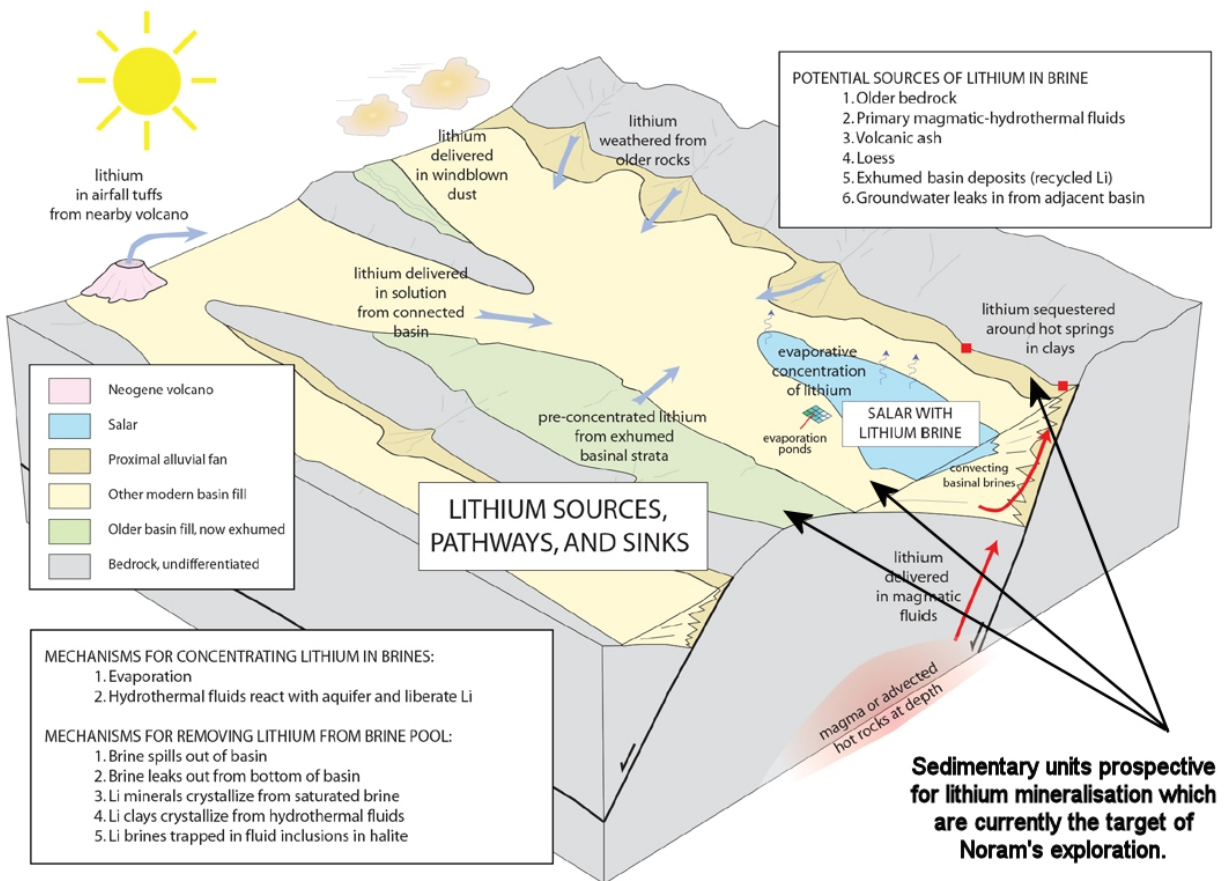


Figure 7 – Schematic deposit model for lithium brines (Bradley, 2013).



Figure 8 – Example of gypsum (?) blebs in a tuffaceous, calcareous mudstone.



Figure 9 – Example of algal mats in the Esmeralda Formation on the Zeus claims.



Figure 10 – Digitate algal structures in the Esmeralda Formation on the Zeus claims.

8 Deposit Types

Noram's Clayton Valley claims offer two deposit types that are potential objects of exploration efforts. Type one is the most obvious, which involves drilling for brines in the deep basin similar to those being exploited by Albemarle at their operations at Silver Peak. The lithium brine potential of Noram's claims has not been investigated to date.

The second deposit type depends on the development of a new lithium extraction process currently being developed. The process has been tested at the bench scale by Membrane Development Specialists at their laboratory in Escondido, California (Section 13). The process being tested would extract lithium directly from lithium-rich mudstones and claystones, which occur at surface over large portions of the southeastern claim groups – particularly identified on the Zeus claims. The same or similar beds appear to occur beneath the surface over large areas of at least some of the other claim groups.

9 Exploration

Competitor companies are known to be active in the Clayton Valley. They are sampling and performing geophysical surveys and drilling, among other activities. As far as is known, competitors are mostly searching for the deeper brine targets. Cypress Development Corporation

is the only other company in the Clayton Valley, besides Noram, known to be investigating lithium-rich sediments occurring at surface. In August 2016 Cypress optioned part of their Clayton Valley properties to Pure Energy Minerals (cypressdevelopmentcorp.com news releases). The portion they optioned had a higher potential for discovery of the deep basinal brines. The portion they kept is discussed further in Section 23.

At this point in time, the only exploration activity conducted by Noram on its claims has been:

1. Three phases of surface sampling with assaying of all surface samples
2. Collection of surface bulk samples for testing by Membrane Development Specialists and by other labs
3. Completion of a shallow drilling program on its Zeus claim group (as described in Section 10 below)

The exploration work has been primarily conducted by the author as a contractor, working alongside and through Harrison Land Services. No detailed geologic mapping, per se, has been undertaken, although various geologic phenomena have been noted and photographed.

The primary objective of the exploration program has been to establish the presence of high lithium values in sediments over a large area of the Noram claims.

9.1 Surface Sampling Method and Approach

As the property was considered a raw prospect, the object of the surface sampling performed during 2016 was to establish the presence or absence of lithium and perhaps other minerals of value in the surface sediments. Sampling took place in three phases which started with grab samples, progressed to grab and chip samples to characterize mineralization over stratigraphic intervals and finally with 50-kilogram samples which were utilized in metallurgical tests to demonstrate the viability of liberating lithium from the clay while separating magnesium and calcium from the resulting pregnant solution.

In most cases, particularly for the chip samples, an attempt was made to clear away the surficial weathered material to obtain the freshest sample available. It should be noted that the surface weathering in this region was believed to be quite deep, however the drilling proved that quite the opposite was true. Sampling methods are more thoroughly described in the previous Technical Reports filed by Noram and Alba.

All surface sampling was conducted by or was closely supervised by the author. The sampling was completed in three phases. All phases used handheld GPS units to locate the sample sites.

- Phase 1 was a first pass effort to see if any of the sediments were lithium-rich. It consisted of the collection of 17 random grab samples from the Spartan and Zeus claim groups.
- Encouraged by the results from the Phase 1 samples, Phase 2 involved a more intense sampling effort with the main objective of determining how consistently the lithium mineralization occurs. Some 81 samples were collected during Phase 2, primarily from

the Zeus claim group, but also from the Zeus Extension, Spartan and Hades claim groups. Many of the samples collected in Phase 2 were vertical chip samples and many of these were stacked vertical intervals – one occurring above or below that last on the sides of the washes. Sample sites were marked on the ground, located using a handheld GPS and were photographed.

- Phase 3 of the surface sampling program consisted of the collection of two bulk samples of approximately 50 kilograms (110 pounds) each from two different sites. The samples were shipped to Membrane Development Specialists for lithium extraction testing. Also during Phase 3 some 4 additional vertical chip samples were collected on the Zeus claims. Geologic investigations on the Zeus claims appeared to show that marker beds were present within the lithium-rich sediments that would enable correlation of beds between the planned drill holes, however this did not prove to be true from the drill hole information. Drill holes were also staked during Phase 3 in order to allow the permitting process to begin for the projected drilling phase.

Details of the three phases of surface sampling and collection of two bulk samples were enumerated in two previous NI 43-101 reports (for Noram Ventures Inc., dated October 24, 2016 and for Alba Minerals Ltd., dated January 13, 2017). The reports contained sample locations, sample descriptions and analyses. To avoid unnecessary redundancy, these details will not be repeated herein.

On completion of the surface sampling phases, the author prepared a report for Noram according to the requirements of Canada's National Instrument 43-101, entitled "Lithium Exploration Project, Clayton Valley, Esmeralda County, Nevada, USA" and dated 24 October, 2016. The report was filed on SEDAR in November, 2016.

In the report the author recommended that Noram conduct a drilling program of approximately 55 holes of approximately 70 feet (21.3 meters) depth to begin quantifying the volume and grade of the lithium-bearing sediments on the Zeus and Hades claims. Permits were obtained for the recommended drilling program, and the drilling program, which is described in Section 10 below commenced in early December, 2016.

Following the agreement between Noram and Alba described in Section 4, a similar Technical Report to the one prepared for Noram was filed for Alba and Noram and filed with SEDAR in February 2017. It also contained details of the drilling program up to the effective date of the report, which was January 13, 2017.

10 Drilling

Drilling on Noram's claims commenced on the 13th of December with a plan to drill 55 sites. During the Phase 1 drilling program 46 holes were completed, rather than the planned 55 holes. The average hole depth was 14.3 meters. Forty-four of the holes (labeled CVZ-01 through CVZ-44) were drilled on the Zeus claims. One hole, drilled on the Hades claims and labeled CVH-01, was located near the old shaft described in the previous two Technical Reports. One hole was

also drilled in the area of the Zeus Extension claims. It was originally thought that this hole was on the Zeus Extension claims and was therefore labeled CVX-01. It was later found that it was located just off of the Zeus Extension claims, on the Zeus claims. Table 5 lists the boreholes drilled, Figure 11 is an overview map of all of the Phase 1 drill holes and Figure 12 shows an enlarged view of the collar locations of each hole drilled on the Zeus claims.

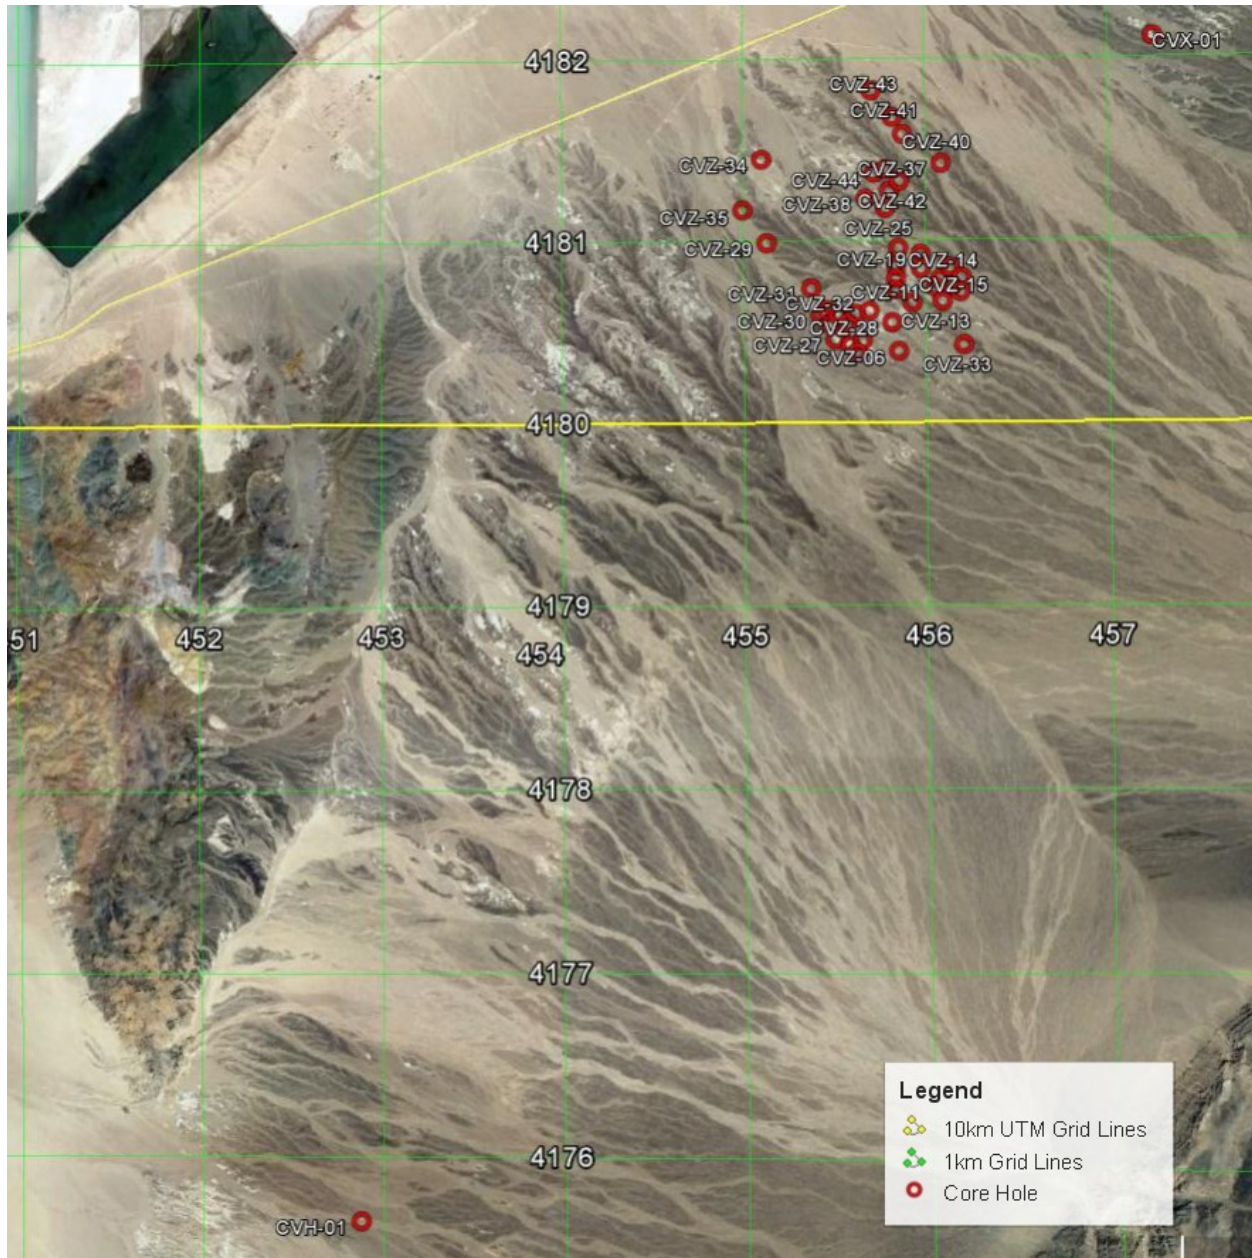


Figure 11 - Locations of the 46 sites drilled during the Phase 1 drilling campaign.

The grid displayed in Figure 11 is UTM NAD 83, Zone 11S with 1000 m spacing. Photo source – Google Earth Pro. Grid source = Nearby.org.uk.

Table 5 – Phase 1 core hole location data.

Locations in UTM, NAD83, Zone 11S.

Hole ID	Easting	Northing	Elevation (m)	Total Depth (m)
CVH-01	452876.5	4175657.0	1378.0	14.3
CVX-01	457245.5	4182107.8	1377.0	8.2
CVZ-01	455519.9	4180580.7	1328.6	15.1
CVZ-02	455569.5	4180543.4	1329.5	14.6
CVZ-03	455584.7	4180421.6	1334.0	14.5
CVZ-04	455651.8	4180445.2	1335.0	14.0
CVZ-05	455622.2	4180380.1	1336.7	13.4
CVZ-06	455850.7	4180385.6	1343.7	11.0
CVZ-07	455614.6	4180595.0	1332.5	14.6
CVZ-08	455690.3	4180608.0	1333.1	14.5
CVZ-09	456074.6	4180778.3	1343.0	15.2
CVZ-10	455973.0	4180837.4	1339.2	10.7
CVZ-11	456051.0	4180737.3	1344.3	12.2
CVZ-12	456143.2	4180742.4	1345.7	12.2
CVZ-13	456091.0	4180658.0	1347.0	12.8
CVZ-14	456131.2	4180845.8	1343.4	13.4
CVZ-15	456187.3	4180710.1	1348.9	12.2
CVZ-16	456196.1	4180790.9	1346.1	16.8
CVZ-17	455850.3	4180951.7	1335.4	15.8
CVZ-18	455835.2	4180723.9	1338.8	15.8
CVZ-19	455971.7	4180918.5	1339.5	14.6
CVZ-20	455837.8	4180851.7	1333.8	27.1
CVZ-21	455961.7	4180720.2	1340.7	15.2
CVZ-22	455926.0	4180650.8	1342.0	12.2
CVZ-23	455837.3	4180785.9	1337.5	13.7
CVZ-24	456031.3	4180594.5	1346.0	15.2
CVZ-25	455780.8	4181171.1	1330.6	15.2
CVZ-26	455479.0	4180533.1	1328.2	15.5
CVZ-27	455504.0	4180452.5	1330.9	6.7
CVZ-28	455814.5	4180544.1	1342.0	14.9
CVZ-29	455129.8	4180984.9	1315.9	12.2
CVZ-30	455421.0	4180593.0	1327.5	15.2

CVZ-31	455373.0	4180734.2	1323.8	15.2
CVZ-32	455454.6	4180613.8	1326.5	15.2
CVZ-33	456205.5	4180418.8	1354.0	28.0
CVZ-34	455103.5	4181446.1	1305.7	14.0
CVZ-35	454998.5	4181166.9	1310.5	15.2
CVZ-36	455782.3	4181387.1	1323.8	13.4
CVZ-37	456086.2	4181416.3	1334.5	15.2
CVZ-38	455673.6	4181224.7	1321.5	13.4
CVZ-39	455802.1	4181266.9	1331.3	15.2
CVZ-40	455878.0	4181578.2	1325.2	14.6
CVZ-41	455821.1	4181672.6	1321.7	12.2
CVZ-42	455858.8	4181319.8	1328.7	15.2
CVZ-43	455706.6	4181821.3	1315.4	9.4
CVZ-44	455718.3	4181366.6	1328.8	13.7

Drill holes were located using a Trimble GPS Pathfinder ProXT unit.

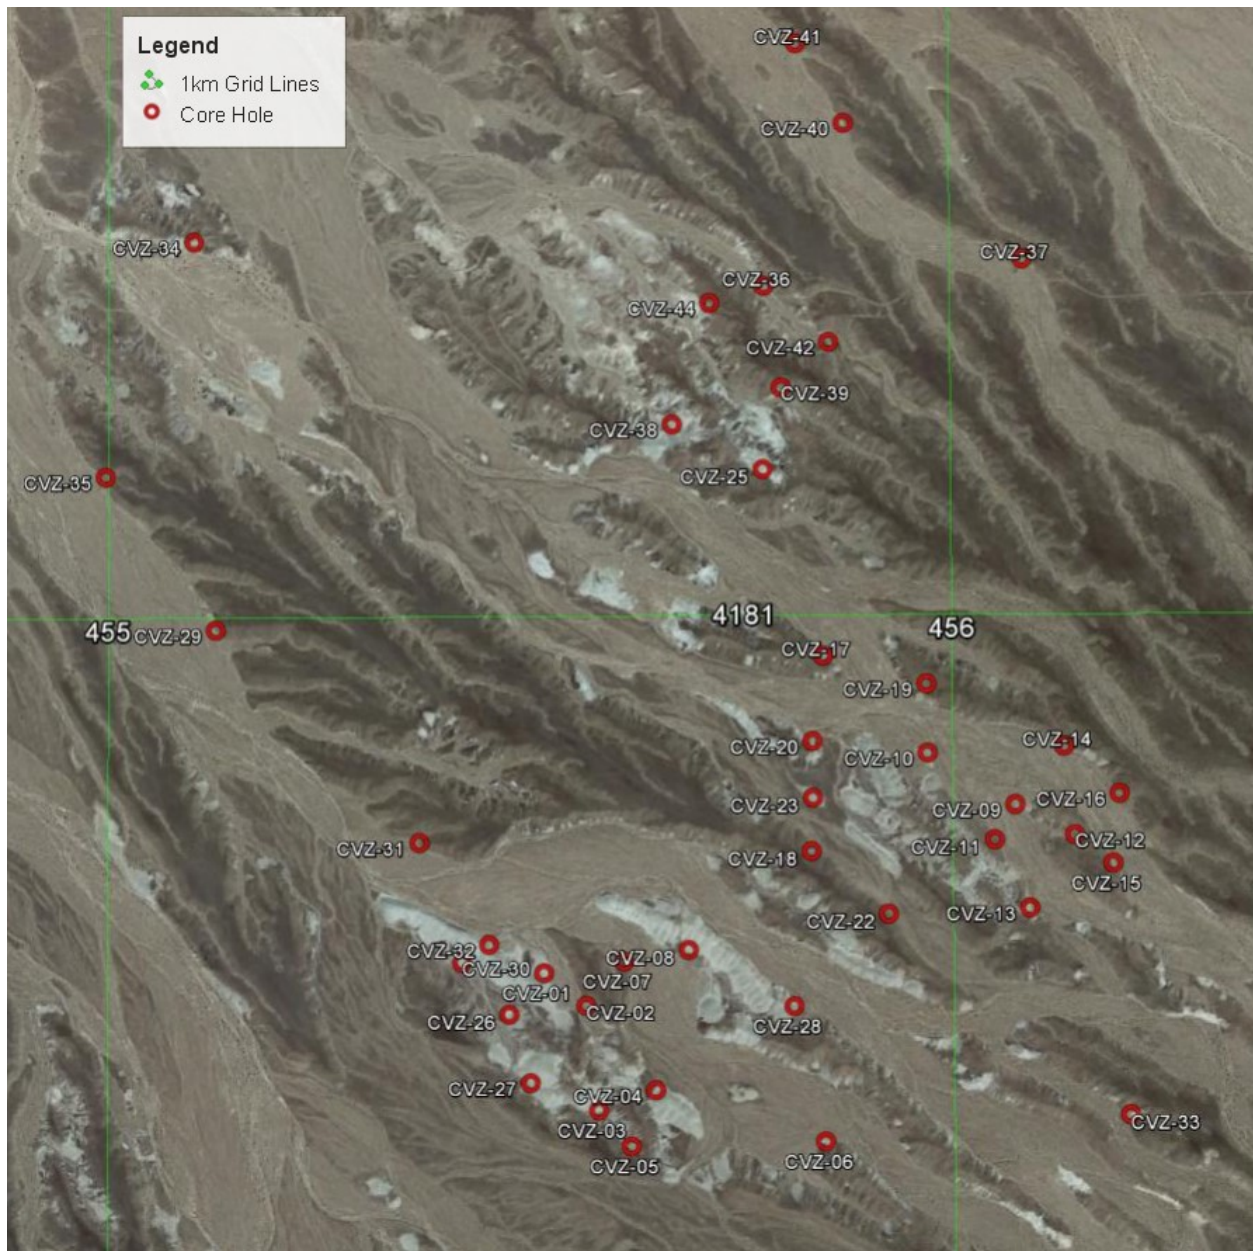


Figure 12 - Enlarged map of collar locations of the 44 core holes drilled on the Zeus claims.

The grid displayed in Figure 12 is UTM NAD 83, Zone 11S with 1000 m spacing. Photo source – Google Earth Pro. Grid source = Nearby.org.uk.

A total of 544 core samples and 44 QA/QC samples were dispatched to the ALS laboratory in Reno for analysis.

Drilling was carried out by Harrison Land Services using equipment manufactured by Shaw Tool. The drills are “backpack” type drills using 2-cycle engines for power. They drilled a 41-

mm core to depths sometimes surpassing 90 feet (27.4 m). Figure 13 shows one of these drills in operation on the subject property.



Figure 13 - Shaw Tools backpack core drill in operation on the Zeus claims.

Two of these drills were operating for most of the 10 days prior to the holiday break in December. After the break, drilling resumed on January 3, 2017 using 3 drills most of the time until drilling finished on January 24. As with most drilling operations, difficulties were encountered. Most of the rock is poorly lithified and often comes out of the core tube as a soft mud or clay, making recovery problematic at times. Despite this, core recovery averaged 80.1% for all 46 drill holes.

The terrain in the area of close-spaced holes consists of elongate, rounded hills cut by washes (Figure 6). Attempts to drill from the tops of these hills or down in the washes proved to be problematic for the small drills since the hills are topped by very hard, silicic, unconsolidated rubble that had washed down from the surrounding mountain ranges and the washes contained similar unconsolidated rocks. For this reason, all the holes in the close-spaced drilling area were drilled along the base of the hills, but up out of the washes proper.

11 Sample Preparation, Analyses and Security

Core samples were collected from the drillsites by the geologists on the project, including the author of this report, and were transported to the staging area box trailer via ATV. At the trailer the core was logged for RQD, and lithology. The core was then photographed. The core was split by the onsite geologists. Half of the core was retained in the core boxes for future viewing or sampling. The other half of the core was placed in consecutively numbered sample bags, along with numbered sample tags, to be shipped to the same ALS laboratory in Reno as was utilized for surface samples. The site where logging, photography and sampling occurred is picture in Figure 14, along with geologist Michael Keller who assisted the author during the drilling project.

Normally, samples would be separated along lithologic breaks in the core. These samples were different in that, for most of the samples, no definite lithologic breaks could be discerned. Therefore, samples were almost entirely collected at 4-foot intervals. The lack of lithologic breaks is consistent with the geologic model of a playa lakebed sediment and since the close-spaced drill holes only tested approximately a 15-meter thick section of the sediments.

There were indications from Noram's and Noram's competitors' testing that the lithium may be taken into solution relatively easily, even with normal deionized water. For this reason, sawing the core was not considered. The core was relatively soft, so it was found that, with some exceptions, the core could be split using a putty knife. Where hard layers or nodules were encountered, the core was split using a hammer and 3-inch wide chisel. It is estimated that the hard layers or nodules constituted about 2% of the core.



Figure 14 – Geologist Michael Keller in box trailer used for core logging and sampling.

The core was only handled by the drillers and the geologists and was locked in the trailer when no one was onsite. Samples for assay were transported back to the author's hotel room where they were secure until shipment to the lab.

For shipment, the bagged samples were placed in 5-gallon plastic pails along with the sample submittal sheets. As an additional security measure, two globe-type metal seals were inserted through the side and top of each pail and sealed. Duct tape was then used to cover the globe seals to prevent accidental damage to the seals during shipment. Figure 15 shows photographs of the sealed shipping containers. A message was taped to the top of each pail indicating that, if the seals were compromised, the lab personnel were to contact the author by phone or email. The pails were then shipped via United States Postal Service to the lab in Reno, NV. There were no indications from the lab that the seals had been compromised.



Figure 15 - Sealed shipping containers, before and after applying duct tape.

All samples were sent to ISO-17025 accredited ALS Laboratories in Reno, Nevada for analysis. ALS is a public company listed on the Australian stock exchange, and is entirely independent of Noram and Alba. All samples were prepared using ALS' PREP-31 sample preparation process, which is presented in the ALS Fee Schedule as:

“Crush to 70% less than 2mm, riffle split off 250g, pulverize split to better than 85% passing 75 microns.”

Each sample was then analyzed using ALS' ME-MS61 analytical method which uses a Four Acid Digestion and MS-ICP technologies. All samples were analyzed for 48 elements. Other than the standard quality control procedures implemented by ALS as part of their ISO-17025 accreditation protocols, no additional quality control procedures were carried out by the operator. Samples were kept in the care of the author at all times until mailed via the United States Postal Service to the ALS lab in Reno.

Four types of QA/QC samples were used:

Table 2 - QA/QC samples used for the Phase 1 drilling.

Sample Type	Number of Samples
MEG-Li.10.13	12
MEG-Li.10.14	6
MEG-Blank.14.03	15
Duplicate samples	11

The MEG samples were purchased from Minerals Exploration & Environmental Geochemistry of Reno, Nevada. Figures 16 and 17 show the distributions of the assay results for the MEG lithium standards. All values fell within the high and low range values determined by MEG from MEG's 117 test samples for each of MEG-Li.10.13 and MEG-Li.10.14. The MEG standards were processed by ALS Laboratories in Vancouver, BC using aqua regia digestion.

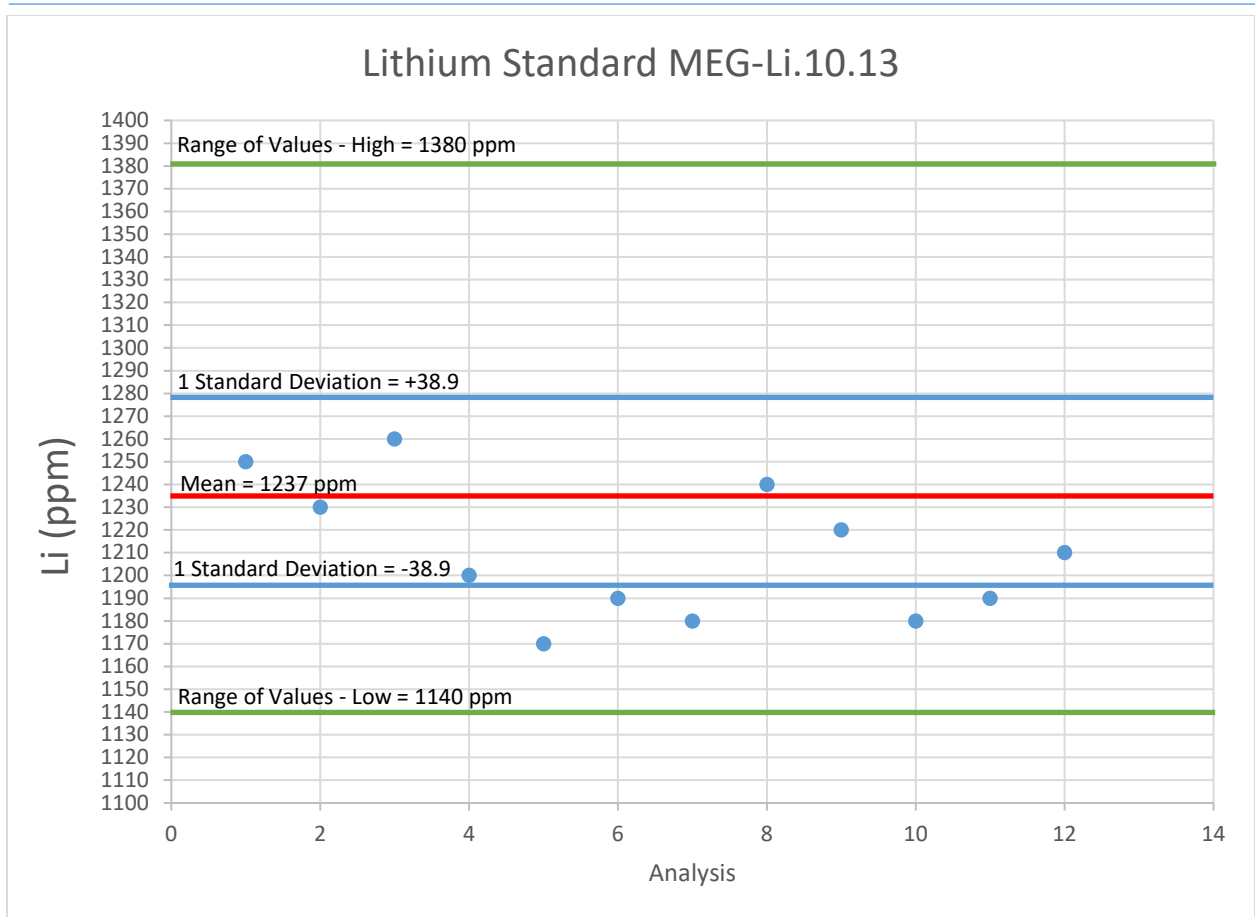


Figure 16 - Range of values for MEG-Li.10.13.

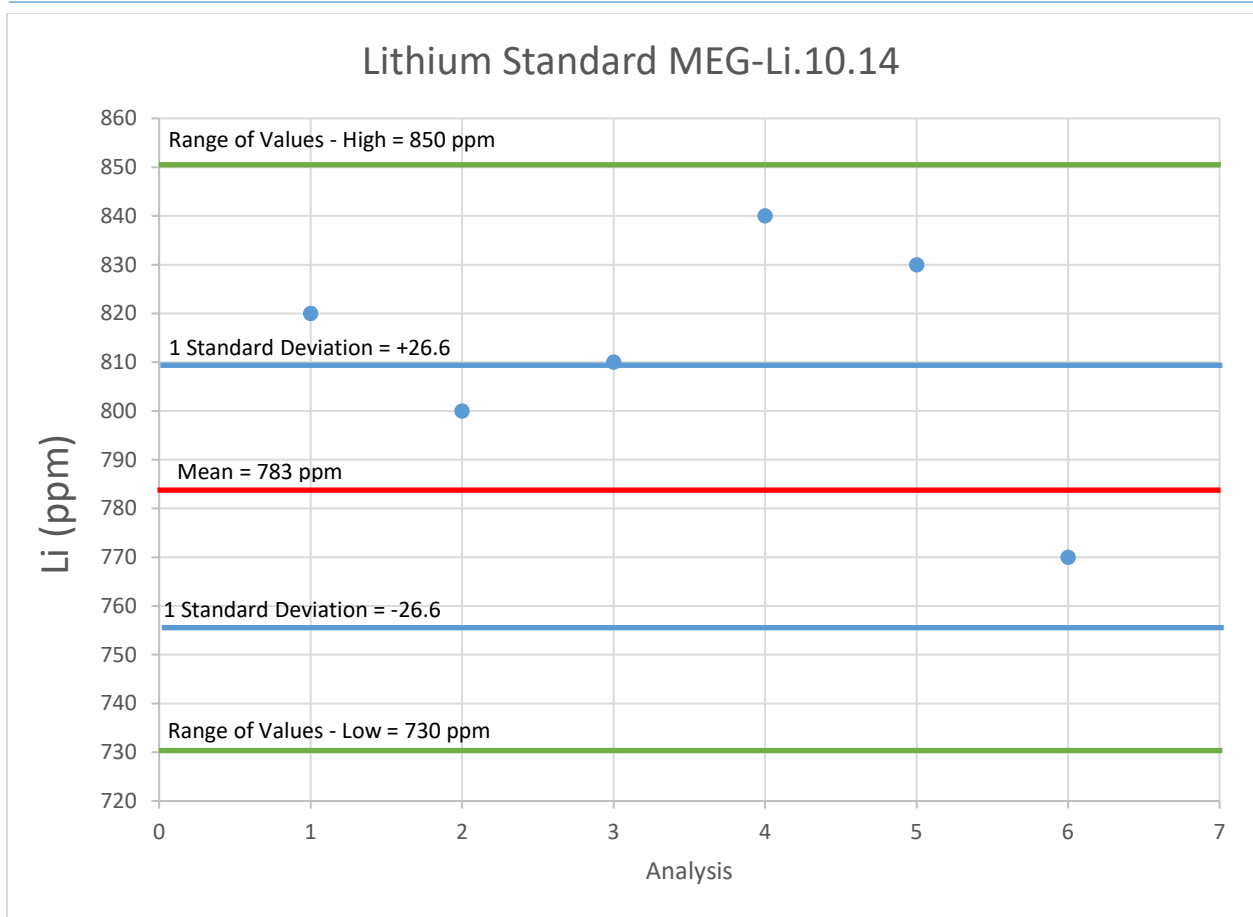


Figure 17 - Range of values for MEG-Li.10.14.

Fifteen MEG Blank Standard 14.03 samples were used as QA/QC samples during the drilling program. All Blank sample results were judged to be within an acceptable range. The distribution of lithium values from the blank sample results is shown in Figure 18.

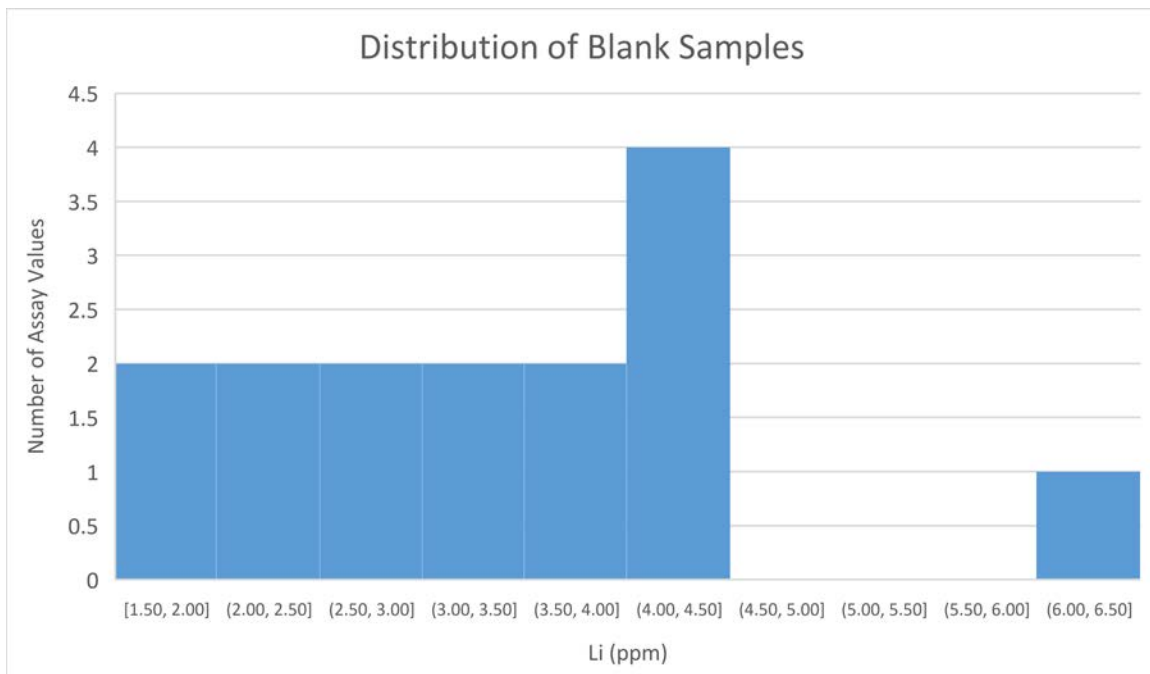


Figure 18 - Distribution of Blank Standard results.

Duplicate samples were obtained by collecting $\frac{1}{2}$ of the $\frac{1}{2}$ core remaining after splitting the sample for assay. Most duplicate sample results were very close to the original sample results. The largest variation was 9.9% between one sample pair. The next largest sample pair variation was 3.5%. These results were judged to be acceptable. Figure 19 is a graph showing the relationship between sample pairs.

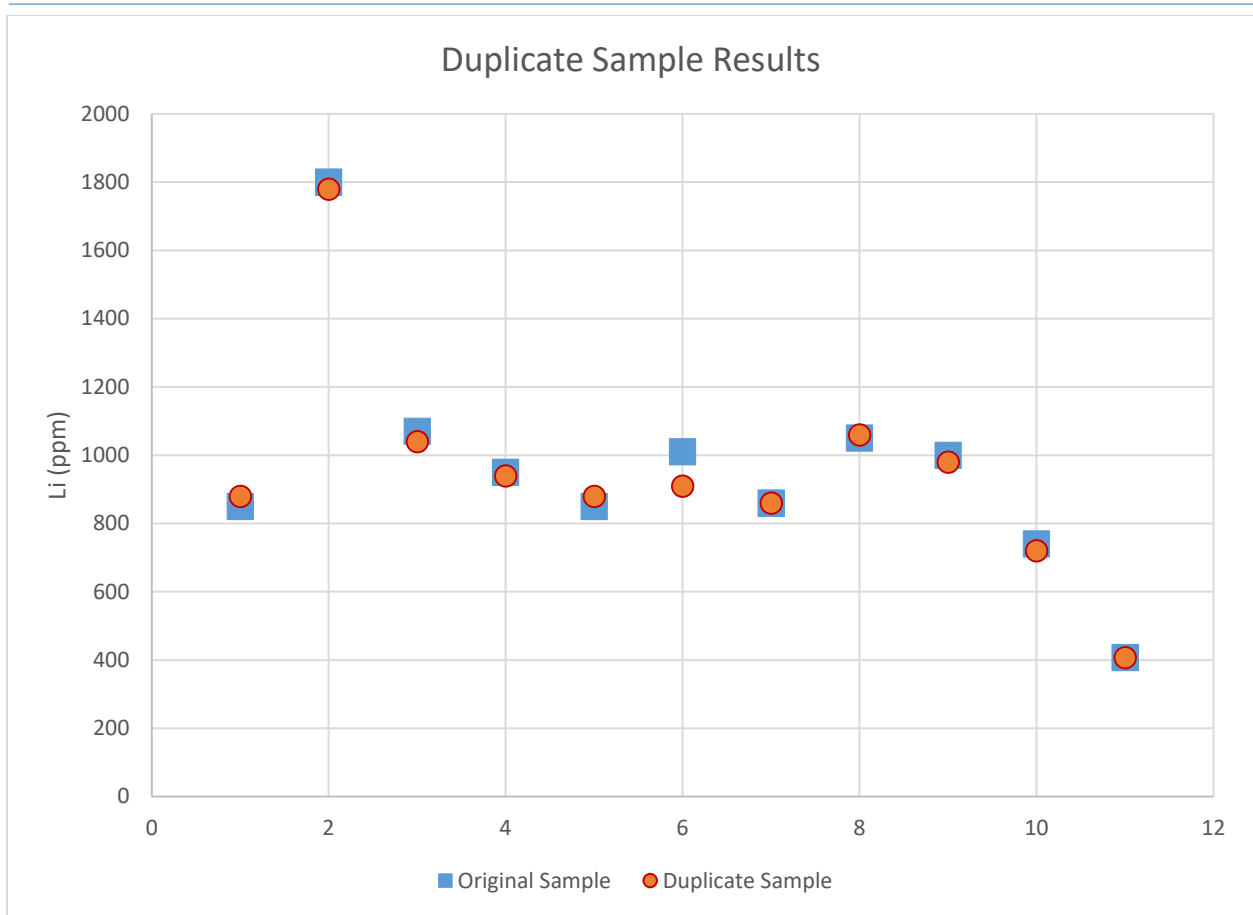


Figure 19 - Comparison of duplicate sample pairs.

12 Data Verification

In regard to the drilling program, the author has been able to confirm the accuracy of locations of drill holes by checking a number of them with his own handheld GPS unit. During his visits to the property during the drilling program, the author confirmed that sampling was being conducted according to the protocols described in Section 11 above, and therefore data collected on drill samples to date is accurate.

Assay data used in the Inferred Mineral Resource model was cross-checked against the original assay certificates after the data had been imported into the model and spot checked the assay values displayed in cross sections. Cross sections of the model were generated and volumetrics checked by the cross-sectional method to verify the model's accuracy.

The author is of the opinion that there have been no limitations on his verifying any of the data presented in this report, except for his not having verified the resources reported on a neighboring property by Pure Energy Minerals (Blois, 2017). The author is of the opinion that all data presented in this report is adequate for the purposes of this report.

13 Mineral Processing and Metallurgical Testing

Noram commissioned Membrane Development Technologies (MDS) to investigate the amenability of the subject property's sediments to lithium extraction using new membrane processes. MDS was provided with three bulk samples for testing. Two of the samples were collected from the same surface sample site on the Zeus claims. The other sample was taken five kilometers to the southwest in order to provide preliminary assurance that spatial variation in mineralogy across Noram's claims, which may affect Li recoverability, could be taken into account. The three samples had mean Li grades of 917ppm, 933ppm and 940ppm Li. The first two samples (917ppm and 933 ppm) were estimated from three samples collected at each sampled site. The last sample was thoroughly homogenized in the laboratory at SGS Labs' Denver facility and is the average of six splits taken from the homogenized sample which averaged 960 ppm Li. These samples are considered to adequately represent the target mineralization considering the early stage of exploration of the property.

Two confidential internal reports by MDS (Lein, 2016 and 2017) and a recent report by AuTec (Baron, 2017) summarizing and explaining the MDS work, although preliminary in nature, have shown that the test samples were amenable to an acid leach, ultrafiltration, nanofiltration and reverse osmosis to separate the lithium from the test material and remove a large portion of the magnesium and calcium with no rejection of lithium. These bench-scale tests focused on the viability of liberating lithium from the clays while removing magnesium and calcium (the only potentially deleterious elements evaluated to date) from the leachate. The tests on the third sample (960ppm Li) have indicated that it is possible to recover approximately 86.5% of the lithium from the sample. The tests also show that 77.7% of the acid and 78.4% of the water used in the process will be recyclable. These two factors have been shown to be of primary importance to the economic viability of the process and the project as a whole. In addition, a batch of lithium-rich material can be processed to a lithium carbonate product in the timeframe of a few days, as opposed to several months for processes using evaporation methods. The results are encouraging, but are preliminary and a significant amount of additional testing is required before a final process flow sheet can be determined and the economic viability of the process can be firmly established.

Nonetheless, MDS was able to supply some initial estimates of the costs to process the sample material to recover a metric tonne of lithium carbonate. The MDS estimate for operating costs for the processing was US\$2,045 per short ton (US\$2,255 per metric tonne) of lithium carbonate. This estimate only includes the operating costs for the recovery process and does not include mining and other operational costs. The costs, along with other cost estimates, are used to show the potential economic viability of the project (See Section 14.2).

It is the opinion of the author that, using the approximate calculation of the cost to produce a tonne of lithium carbonate by the MDS process and considering the projected low cost of mining the clays, the property has a reasonable prospect of producing lithium carbonate at some point in the future and could become a low-cost producer. However, a considerable amount of additional

testing will be required to verify its economic viability. Testing is ongoing and is expected to result in a more definitive statement about the test results in the near future.

As a further important point of interest, the process being developed by MDS, once operating, requires the addition of a relatively small amount of make-up water (See discussion in Section 24).

13.1 Li vs. Ca Correlation

Since it appears that the sulfuric acid consumption will, by far, be the single highest cost factor to the lithium extraction process, it is important to examine acid consumption data. The presence of carbonate minerals in the host material is the major influence on acid consumption. None of the samples tested from the drilling were tested for carbonate (CO_3), however one can derive a very near match for the abundance of carbonate by studying the calcium and magnesium data, since nearly all of the carbonate is tied up in the minerals calcite (CaCO_3) and dolomite ($\text{CaMg}(\text{CO}_3)_2$).

By modelling calcium as was done for lithium (See Section 14), it was noted that very similar patterns of distribution were evident between the two models. To follow this line of thinking, a correlation coefficient between Ca and Li was generated and found to be +0.35. Additionally, Ca and Mg were added together and compared to Li. That correlation coefficient yielded a figure of +0.54 and the weighted average of the Ca + Mg in the close-spaced holes (See Section 14) was 6.98%. From this we can conclude that, in the playa lake bed where these sediments were deposited, conditions that were favorable for the deposition of carbonates were also favorable for the deposition of lithium. Figure 20 is a graph of the lithium values versus Ca + Mg values from all of the 344 assays from the close-spaced drill holes used in the Inferred Mineral Resource estimate. The data indicate that, in general, where there are areas of higher carbonate, the increased acid costs to process these materials will be offset by higher lithium grades.

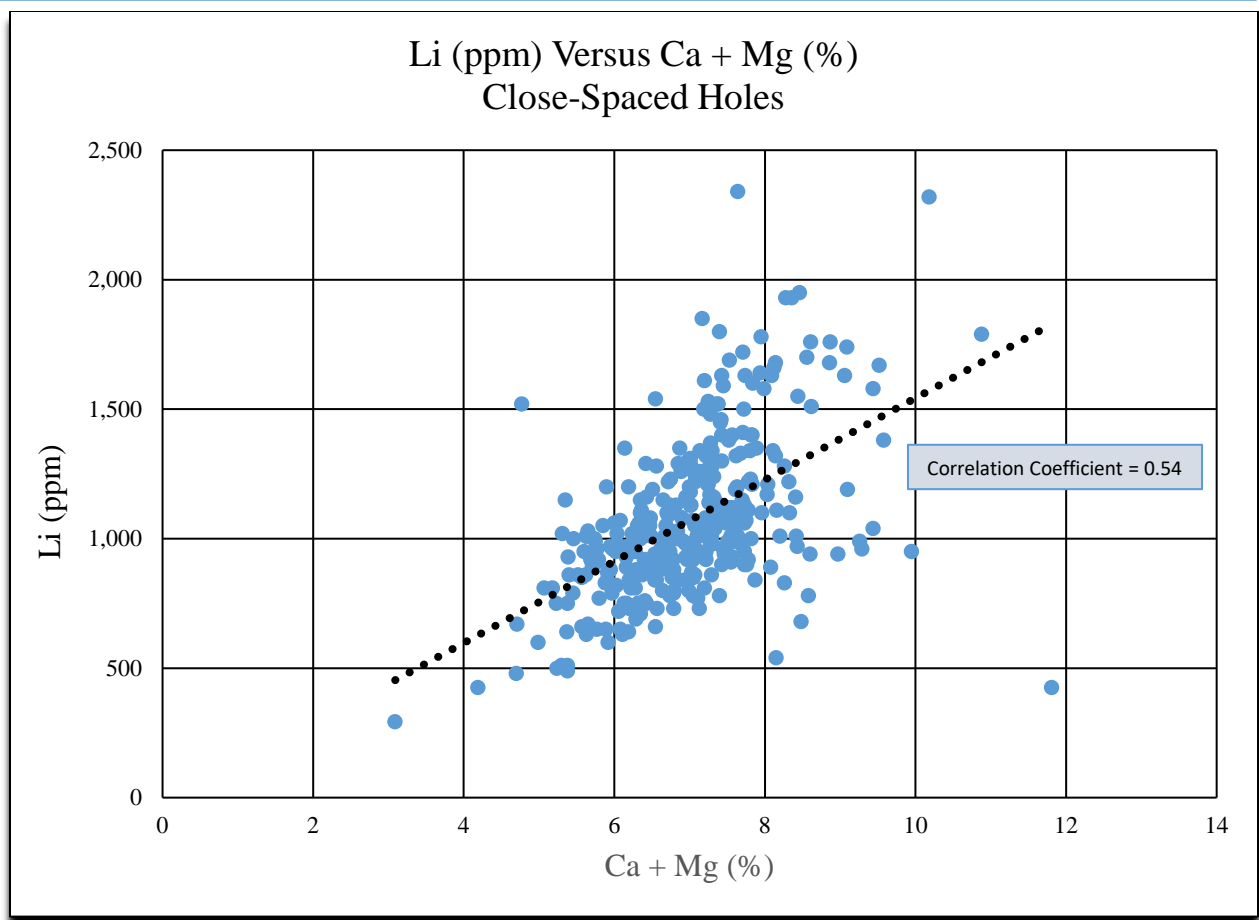


Figure 20 - Graph of Li (ppm) vs. Ca + Mg(%)

14 Mineral Resource Estimates

14.1 General

This Inferred Mineral Resource estimate is considered to be an early stage deposit definition effort. While the factors listed in Section 13 will be important to the possible viability of the deposit, the deposit has not undergone the much more rigorous testing that must be performed before a mining decision can be made.

The deposit is held by placer mining claims staked on U. S. Government lands administered by the Bureau of Land Management. Therefore, the permitting process for any mining operation is well established and has been tested on many past BLM projects. There are no known unusual legal, environmental, socio-economic, title, taxation or permitting problems associated with the subject claims that would adversely affect the development of the property, other than the possible necessity to develop water rights for the extraction of the lithium (See discussion in Section 24).

The Inferred Mineral Resource estimate, herein, is defined by a relatively shallow drilling depth, averaging 14.4 meters and a relatively large areal extent of 455,800 square meters (112.6 acres), determined by an area of close-spaced drill holes. Drill holes outside the area of close-spaced drilling were determined to be too far afield to be of use for the model. The resulting model derived from these parameters is a thin, pancake-like deposit. The close-spaced drill holes have been defined as: CVZ-01 thru CVZ-24, CVZ-26 thru CVZ-28 and CVZ-30 and CVZ-32, making a total of 29 core holes used in the model.

Table 3 - Comparison summary of Close-Spaced Holes to Total Drilling Program

<i>Parameter</i>	<i>Total Phase 1 Drill Program</i>	<i>Close-Spaced Holes</i>
<i>Holes Included</i>	All Holes	CVZ-01 thru CVZ-24 and CVZ-26 thru CVZ-28 and CVZ-30 and CVZ-32
<i>No. of Holes</i>	46	29
<i>Meters Drilled</i>	652	415
<i>Average Hole Depth (m)</i>	14.3	14.4
<i>No. of Samples</i>	544	345
<i>Weighted Average (PPM Li)</i>	907.8	1059
<i>Median (PPM Li)</i>	910	1010

The data for the Inferred Mineral Resource estimate were generated using the Rockworks 17 program, sold by Rockware, Inc.

14.2 Economic Factors

For the development of this inferred mineral resource estimate, consideration has been given to economic factors such as mining and processing costs to determine that the deposit has reasonable prospects for economic extraction. The primary factors for the economic extraction determination are:

- The deposit occurs at or very near the surface, greatly reducing mining costs.
- The deposit is almost entirely unconsolidated or semi-consolidated, which will not require drilling and blasting, but could require ripping with a bulldozer (yet to be determined), further lowering mining costs.
- The mining method that is foreseen would be an open pit involving bulldozers (if required) to rip the sediments and front-end loaders to load the sediments into trucks to be hauled to the processing plant. The size and number of pieces of equipment will be determined by mining engineers once the final size of the operation is determined. The location of the processing plant with regard to the deposit is yet to be determined.
- Preliminary testing for the extraction of the lithium from the mined material (See Section 13) has indicated that the material will be relatively inexpensive to process and the extraction process will use relatively little water (See Section 24).
- From the preliminary testing, the sediments will not require crushing or grinding prior to processing.
- The deposit occurs in a mining-friendly environment, on BLM land, with nearby producing properties.
- Electric power, developed transportation routes and a mining workforce are located proximally to the deposit.

A conservative estimate of the mining cost is between US\$1.50/tonne and US\$2.00/tonne. This estimate is based on three gold (\pm silver) projects in the desert southwest of the United States that have recently undergone economic analyses. These projects are:

- Moss Gold-Silver Project, Mojave County, Arizona - Feasibility Study 2015
 - Owner = Northern Vertex Mining Corporation
 - Host Rocks = Monzonite to Quartz Monzonite
 - Stripping Ratio = 1.6:1
 - Mining Cost per Tonne of Ore = US\$5.96
 - Mining Cost per Tonne Overall = US\$2.29
- Hasbrouck Project, Esmeralda County, Nevada - Pre-Feasibility Study 2016
 - Owner = West Kirkland Mining Inc.
 - Host Rocks = Tuffs and Epiclastic Sediments
 - Stripping Ratio = 1.1:1
 - Mining Cost per Tonne of Ore = US\$3.62
 - Mining Cost per Tonne Overall = US\$1.72
- North Bullfrog Project, Nye County, Nevada - Preliminary Economic Assessment 2016

- Owner = Corvus Gold Inc.
- Host Rocks = Rhyolitic Tuff
- Stripping Ratio = 0.6:1
- Mining Cost per Tonne of Ore = US\$2.41
- Mining Cost per Tonne Overall = US\$1.45

All three of these projects are hosted in much more competent rock than the Noram/Alba Clayton Valley project. All three examples will require drilling and blasting of the ore and overburden, whereas the Noram/Alba project occurs in unconsolidated sediments which will only require some possible ripping with a bulldozer followed by loading into trucks with a front-end loader. Without the necessity to drill and blast solid rock, considerable savings will be realized for the Noram/Alba project. Based on the above information, it is the opinion of the author that using a mining cost of US\$2.00 per tonne for the Clayton Valley project would be a very conservative figure and the actual mining cost could be significantly less.

Table 4 shows estimates of the mining, processing and other operating costs for the average lithium grade of the deposit, based on the mining cost of US\$2.00/tonne, to produce one tonne of lithium carbonate. Processing costs are provided by MDS (Lien, 2016 and 2017). AuTech (Baron, 2017) provided additional analysis of the MDS data (See Section 13).

Table 4 - Estimated costs to produce one tonne of lithium carbonate.

1	2	3	4	5	6	7	8
Material Grade (Li ppm)	Li Metal Per Tonne (kg)	Material Required for 1 Tonne Li ₂ CO ₃ (Tonnes)	Material Required with 86.5% Recovery (Tonnes)	Mining Cost at US\$2.00 per Tonne Material (US\$)	Processing Cost @ US\$10.72 Per Tonne (US\$)	Total Mining + Processing Cost Per Tonne Li ₂ CO ₃ (US\$)	Total Mining + Processing + Other Operating (US\$)
1060	1.06	177	205	\$ 410	\$ 2,198	\$ 2,608	\$ 3,746

Notes:

- Column 1 Average grade of material in the Inferred Mineral Resource model.
- Column 2 Column 1 divided by 1000
- Column 3 1 divided by Column 2 divided by 5.32 times 1000 (5.32 is the multiplier to convert Li metal to Li₂CO₃)
- Column 4 Column 3 divided by 86.5% projected recovery rate
- Column 5 Column 4 times US\$ 2.00 = conservative mining cost per tonne
- Column 6 Column 4 times US\$ 10.72 = projected processing cost from MDS
- Column 7 Column 5 plus Column 6
- Column 8 Column 7 plus estimated operating costs from MDS - includes electric power, membrane elements, man power, sodium carbonate totaling US\$1,138/tonne.

While the numbers in Table 4 are preliminary, they indicate that the cost to produce a tonne of lithium carbonate will be approximately US\$ 3,450/tonne for the average grade of the deposit. With the current price for lithium carbonate in the range of US\$ 14,000 to US\$ 15,500 per tonne (Lithium Miner News for the Month of July 2017)(see also Section 14.3 – Lithium Pricing), it serves to show that there is a reasonable chance that the deposit could be economically exploited.

14.3 Lithium Pricing

Future prices for lithium carbonate is a complicated proposition, given the price rise over the past two years. There appear to be wide variations in the projections of both lithium demand and lithium supply. Due to the projected high future demand for lithium batteries for electric vehicles and other storage devices, lithium prices have soared. Because of the price rise, companies who are producing lithium are increasing their production and there are many start-up companies that are attempting to put lithium deposits into production. With both supply and demand in a state of flux, there are many competing scenarios as to how quickly the new production will come onstream and how rapidly demand will rise. Further complicating the pricing picture is the fact that lithium is mostly sold by private contracts, the terms of which are generally not published.

For this study it was considered most favorable to look at “Consensus Pricing”, or recent price projections of peers and industry analysts as yardsticks to measure the Noram / Alba deposit’s reasonable prospects for eventual economic extraction. The next few paragraphs are examples of “Consensus Pricing” scenarios.

Consensus Pricing Scenario 1


The following excerpt is a quote from the Pure Energy Minerals PEA for Pure Energy’s Clayton Valley Lithium Project (Blois, et al, 2017). The pricing portion of the PEA was generated by lithium market consultant Benchmark Mineral Intelligence Ltd.:

“The major lithium compounds like lithium carbonate and $\text{LiOH}\cdot\text{H}_2\text{O}$ are generally sold under private term contracts and do not have quoted prices on any recognized metals or minerals exchange. The market pricing of these materials is, therefore, somewhat opaque, but it has been widely reported that prices for lithium compounds have doubled in the past 12-18 months, based on shortages of raw material for Chinese conversion facilities to feed their plants to make lithium chemicals for battery makers. Recent reports of $\text{LiOH}\cdot\text{H}_2\text{O}$ prices have been in the range of US\$16,000-\$20,000 per tonne, and even as high as US\$22,000/tonne.”

Benchmark Mineral Intelligence advised using an average 2016 lithium hydroxide price of US\$12,683/tonne for the Pure Energy PEA and this figure was used in the PEA model. Although lithium hydroxide (as used in the Pure Energy model) and lithium carbonate (as used in the Noram / Alba model) command different prices, the graph in Figure 21 shows that they are somewhat comparable.

LITHIUM PRICE

In 2016, lithium prices rose around 300% in China, with contract prices rising to over US\$12,000/t LCE

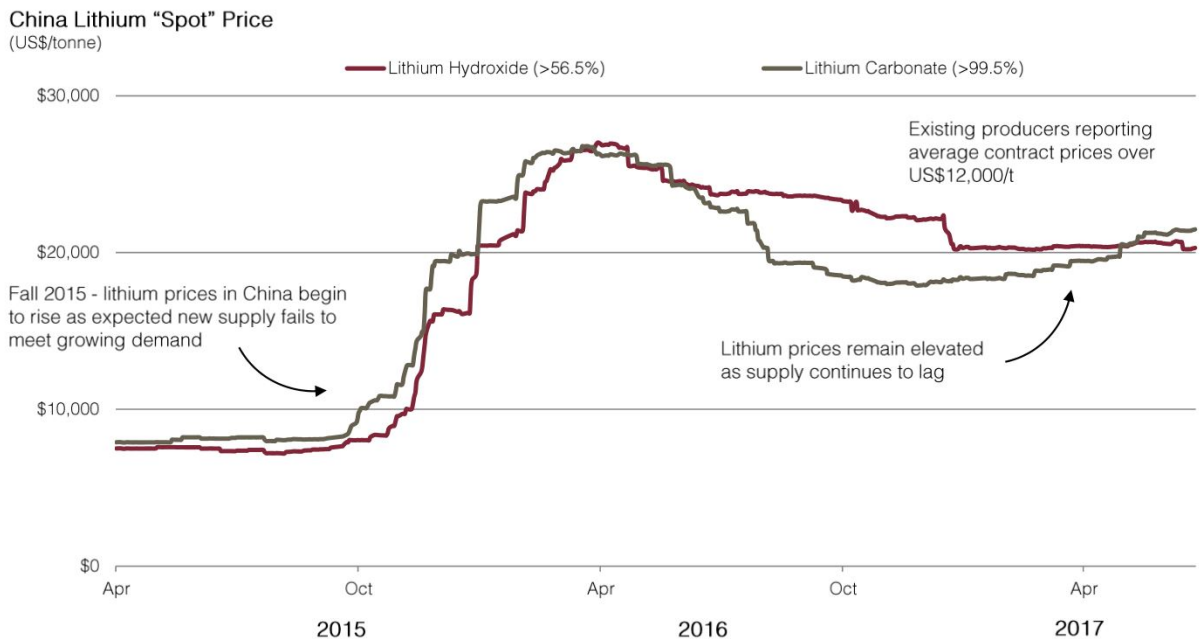

Source: Asian Metal, Thomson Reuters

Figure 21 - China "Spot" prices from Lithium Americas Corp. 2017 AGM presentation.

Consensus Pricing Scenario 2

Avalon Advanced Materials Inc. had a recent PEA prepared by Micon International Limited (Aiken, et al, 2016) with an effective date of October 21, 2016 for their Separation Rapids Project. The report was entitled: "NI 43-101 Technical Report on the Preliminary Economic Assessment of Lithium Hydroxide Production, Separation Rapids Lithium Project, Kenora, Ontario". The price used for the study was US\$11,000/tonne for lithium hydroxide.

Consensus Pricing Scenario 3

Lithium Americas Corporation updated a Feasibility Study with an NI 43-101 Report entitled, "Reserve Estimation and Lithium Carbonate Production at the Cauchari-Olaroz Salars, Jujuy Province, Argentina" with an Effective Date of March 29, 2017 (Burga, et al, 2017). For their economic calculations, Lithium Americas used a projected lithium carbonate price of US\$12,000/tonne.

With pricing predictions varying widely, it was deemed wise to be conservative and choose a projected price for the present study that is somewhat under the three scenarios listed above. For that reason, a price of US\$10,000/tonne of lithium carbonate has been chosen for the purpose of defining a cut-off grade for the Noram / Alba deposit.

14.4 Cut-off Grade

The cut-off grade for the Noram / Alba deposit was calculated by using the cost to produce a tonne of lithium carbonate (See Section 14.2 – Economic Factors) using various lithium grades in the deposit and comparing those values against the projected lithium carbonate price (See Section 14.3 – Lithium Pricing). In this manner, a lithium value of 400 ppm Li was chosen for a cut-off grade. The calculations used for the 400 ppm figure are shown below:

Grade of Deposit Material = 400 ppm Li

Lithium Metal Per Tonne = 0.40 kilograms

Material Required to Produce 1 Tonne of Lithium Carbonate = 470 tonnes (1 ÷ 0.40 X 5.32 X 1000)

Material Required to Produce 1 Tonne of Lithium Carbonate with 86.5% Recovery = 543 tonnes (470 ÷ 0.865)

Mining Cost at US\$2.00/tonne = \$1,087 (543 X \$2)

Processing Cost (Provided by MDS) at US\$10.72/tonne = \$5,824 (543 X \$10.72)

Total Mining + Processing Cost = US\$6,910 (\$1,087 + \$5,824)

Total Mining + Processing + Other Operating Costs = \$8,048 (\$6,910 + \$1,138) (\$1,138 represents the estimated operating costs from MDS and includes electric power, membrane elements, man power, sodium carbonate totaling US\$1,138)

Therefore, the total cost of producing a tonne of lithium carbonate from 400 ppm Li deposit material compares well with the projected price of lithium carbonate of US\$10,000 (See Section 14.4 – Lithium Pricing), leaving a profit margin of US\$1,952/tonne of lithium carbonate produced. From these very preliminary numbers, it is believed that 400 ppm Li is a reasonable cut-off grade for the Noram / Alba deposit.

14.5 Model Parameters

Consider the histogram of the lithium values in the close-spaced holes, generated by Rockworks 17, shown in Figure 21. The statistics for the histogram are listed in Table 5. From these statistics, it was determined that values less than -2 standard deviations (454 ppm Li) would not be used and values greater than +2 standard deviations (1676 ppm Li) would be reduced to 1676 ppm, which in effect, removed or dampened the effect of the moderately anomalous, strongly anomalous and extremely anomalous values from the population. This involved removing or reducing 20 values of the total population of 345 values for the close-spaced holes. This was done to take a conservative approach to the model. So, while the cut-off grade for the deposit was set at 400 ppm Li, based on projected economic factors, none of the samples used in the model had values below the cut-off, making the cut-off a meaningless number with regard to the deposit model.

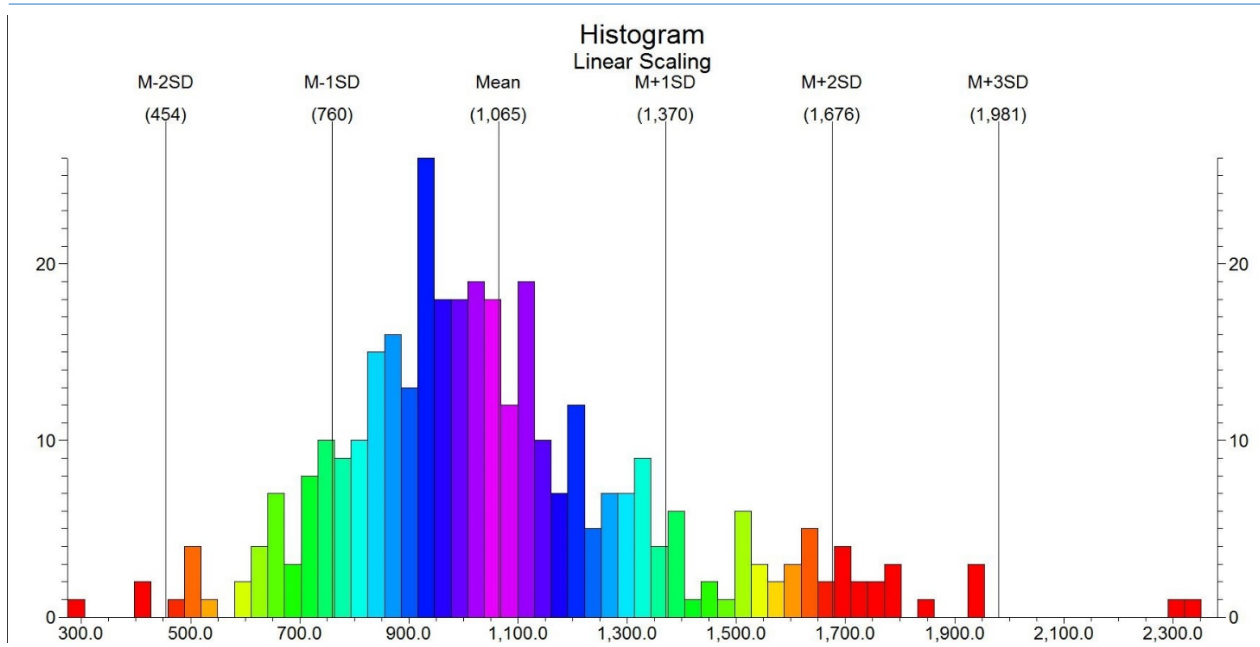


Figure 22 - Histogram of all Li values from close-spaced drill holes.

Table 5 - Statistics for all Li values from close-spaced drill holes.

Statistical Summary	
Population	345
Minimum Value	293.0
Maximum Value	2,340.0
Range	2,047.0
Mean	1,065.02319
Standard Deviation	305.41876
Standard Error	16.44319
Median	1,010.0
Sum	367,433.0
Sum of Squares	423,413,199.0
Variance	93,280.62155
Skewness	0.92889
Kurtosis	1.50207
Coefficient of Variation	0.28677
Mean - 1 Standard Deviations	759.60442
Mean - 2 Standard Deviations	454.18566
Mean - 3 Standard Deviations	148.7669
Mean - 4 Standard Deviations	-156.65187
Mean + 1 Standard Deviations	1,370.44195
Mean + 2 Standard Deviations	1,675.86072
Mean + 3 Standard Deviations	1,981.27948
Mean + 4 Standard Deviations	2,286.69825
Background Population	255
Slightly Anomalous Population	70
Moderately Anomalous Population	18
Strongly Anomalous Population	0
Extremely Anomalous Population	2

Since visibly definable stratigraphic horizons were not found in the core, the model was not constrained by stratigraphy. The vertical thickness of the model was only constrained by the depth of the drill holes. To constrain the model horizontally, a 12-sided polygon was constructed around the close-spaced drill holes at a distance of 100 meters from the outermost holes (Figure 22). It is possible that the model could have been extended farther horizontally, but after careful review of several cross sections and level plans, it appeared that extending the model further was not warranted.

The tops of the drill holes were located in the fringe area between the washes and the elongate ridges, as explained in Section 10. Therefore, the model only includes the volume of material below the level of the washes and does not take into account the ridges of material between the washes. The mass of the material above the washes is estimated to be approximately 2 to 3 million tons, but the data involving the grade of the material (surface sampling) was considered too widespread to be included in the Inferred Mineral Resource model. The material in the ridges does, however, provide considerable upside tonnage potential which may at some future point be included in the Inferred Mineral Resource. However, such potential is conceptual in

nature. There has been insufficient exploration beyond the modeled deposit and it is uncertain if further exploration will result in an enlargement of the deposit.

Figures 23 through 25 are profiles through the inverse distance squared model showing the drill holes and their respective lithium values in PPM. The vertical exaggeration of the profiles in X5 and lithium assays have been composited to 3-meter intervals for display purposes. Careful examination of the profiles, as well as profiles created at right angles, were used to verify the accuracy of the model. Figure 26 shows the locations of the profiles with respect to the drill holes. The profiles demonstrate that, while there is some correlation between nearby holes, correlations do not extend far beyond the holes in a consistent fashion. The one exception to this is a zone of higher grade lithium which trends from southeast to northwest and is visible in the profiles and is shown in the fence diagram of the inverse distance model shown in Figure 27.

Controls on the mineralization are uncertain at this time, but the orientation of the SE – NW higher-grade zone may reflect an ancient shoreline of the playa lake bed. This orientation is also suggestive of the trend of block faulting in the region which also could have influenced lithium mineralization.

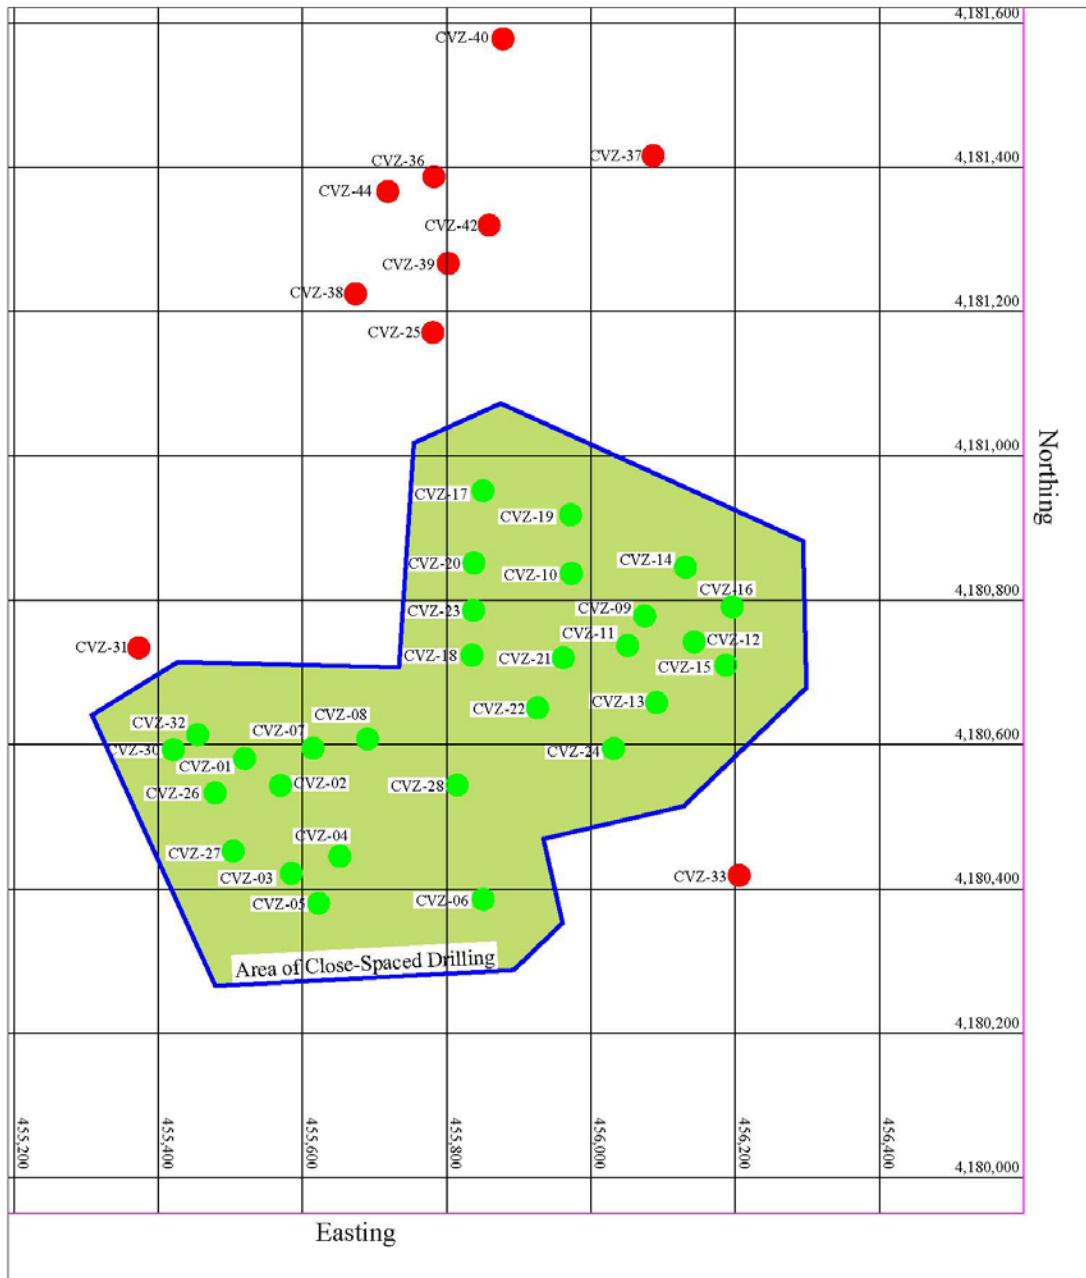


Figure 23 - Polygon used to constrain model horizontally.

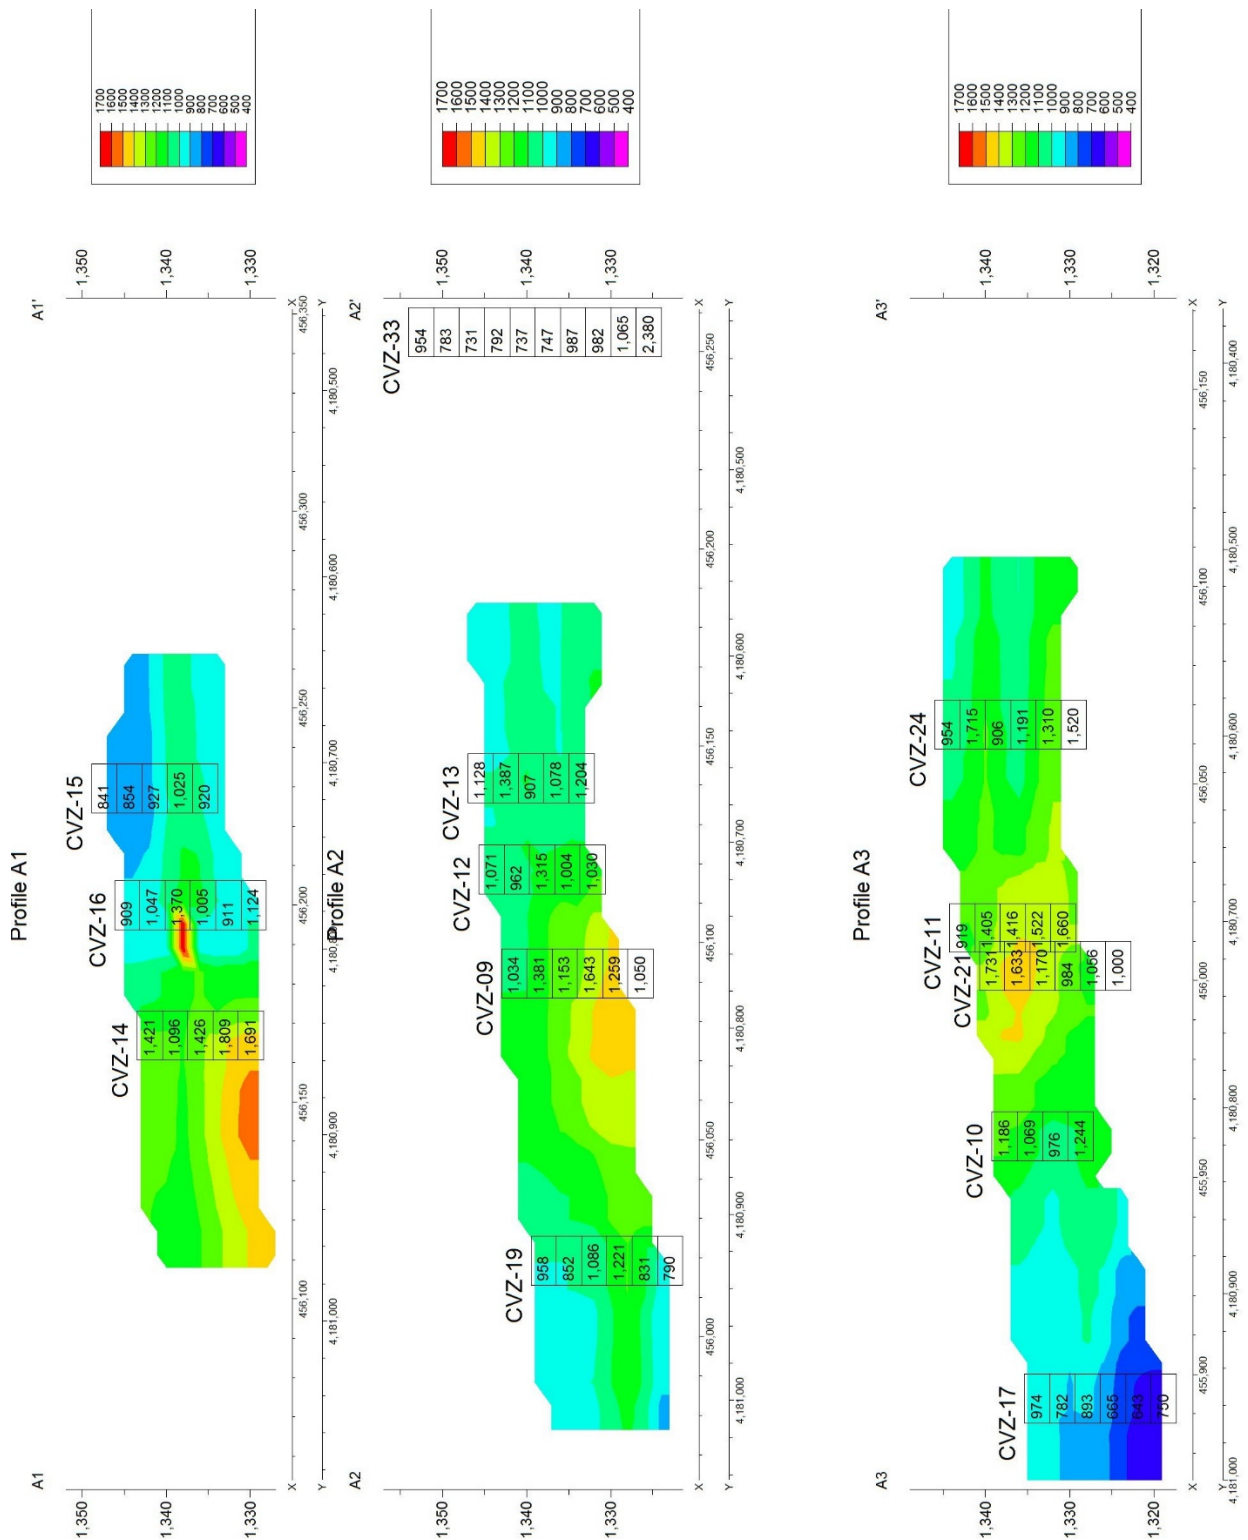


Figure 24 - Profiles A1-A3 through inverse distance model. Vertical exaggeration = 5X.

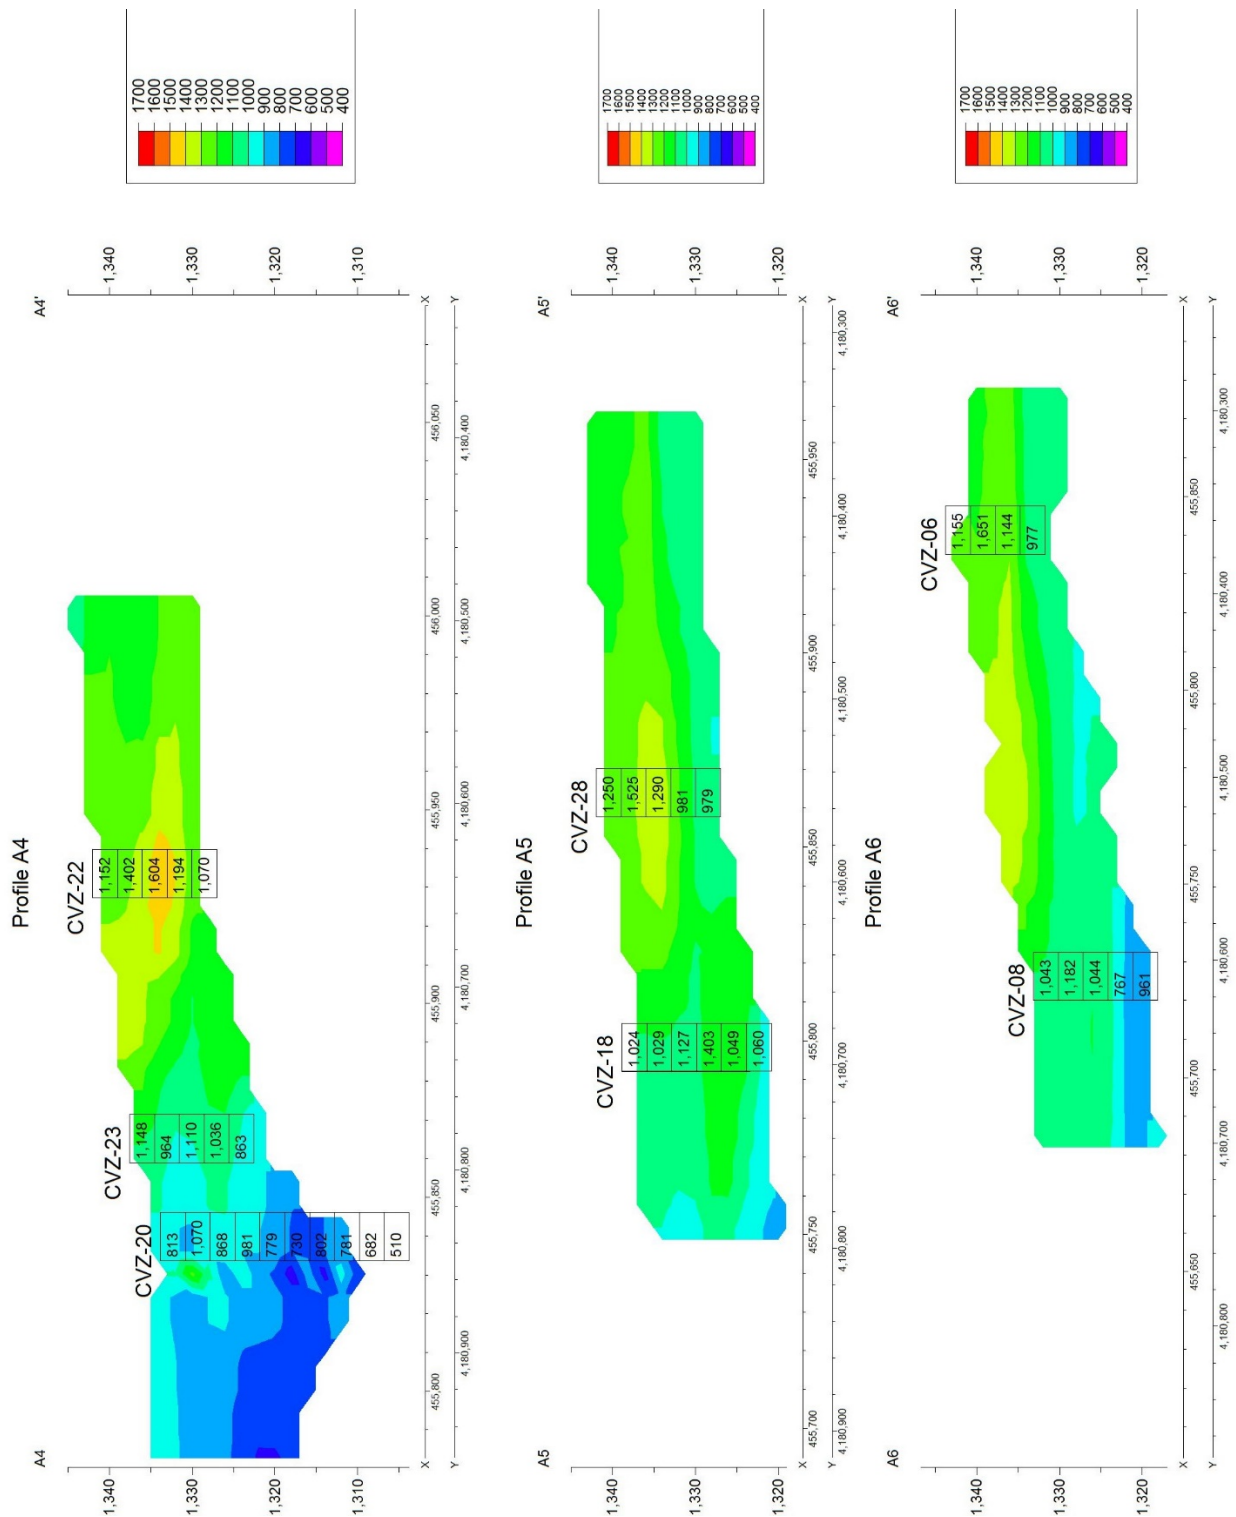


Figure 25 - Profiles A4-A6 through inverse distance model. Vertical exaggeration = 5X.

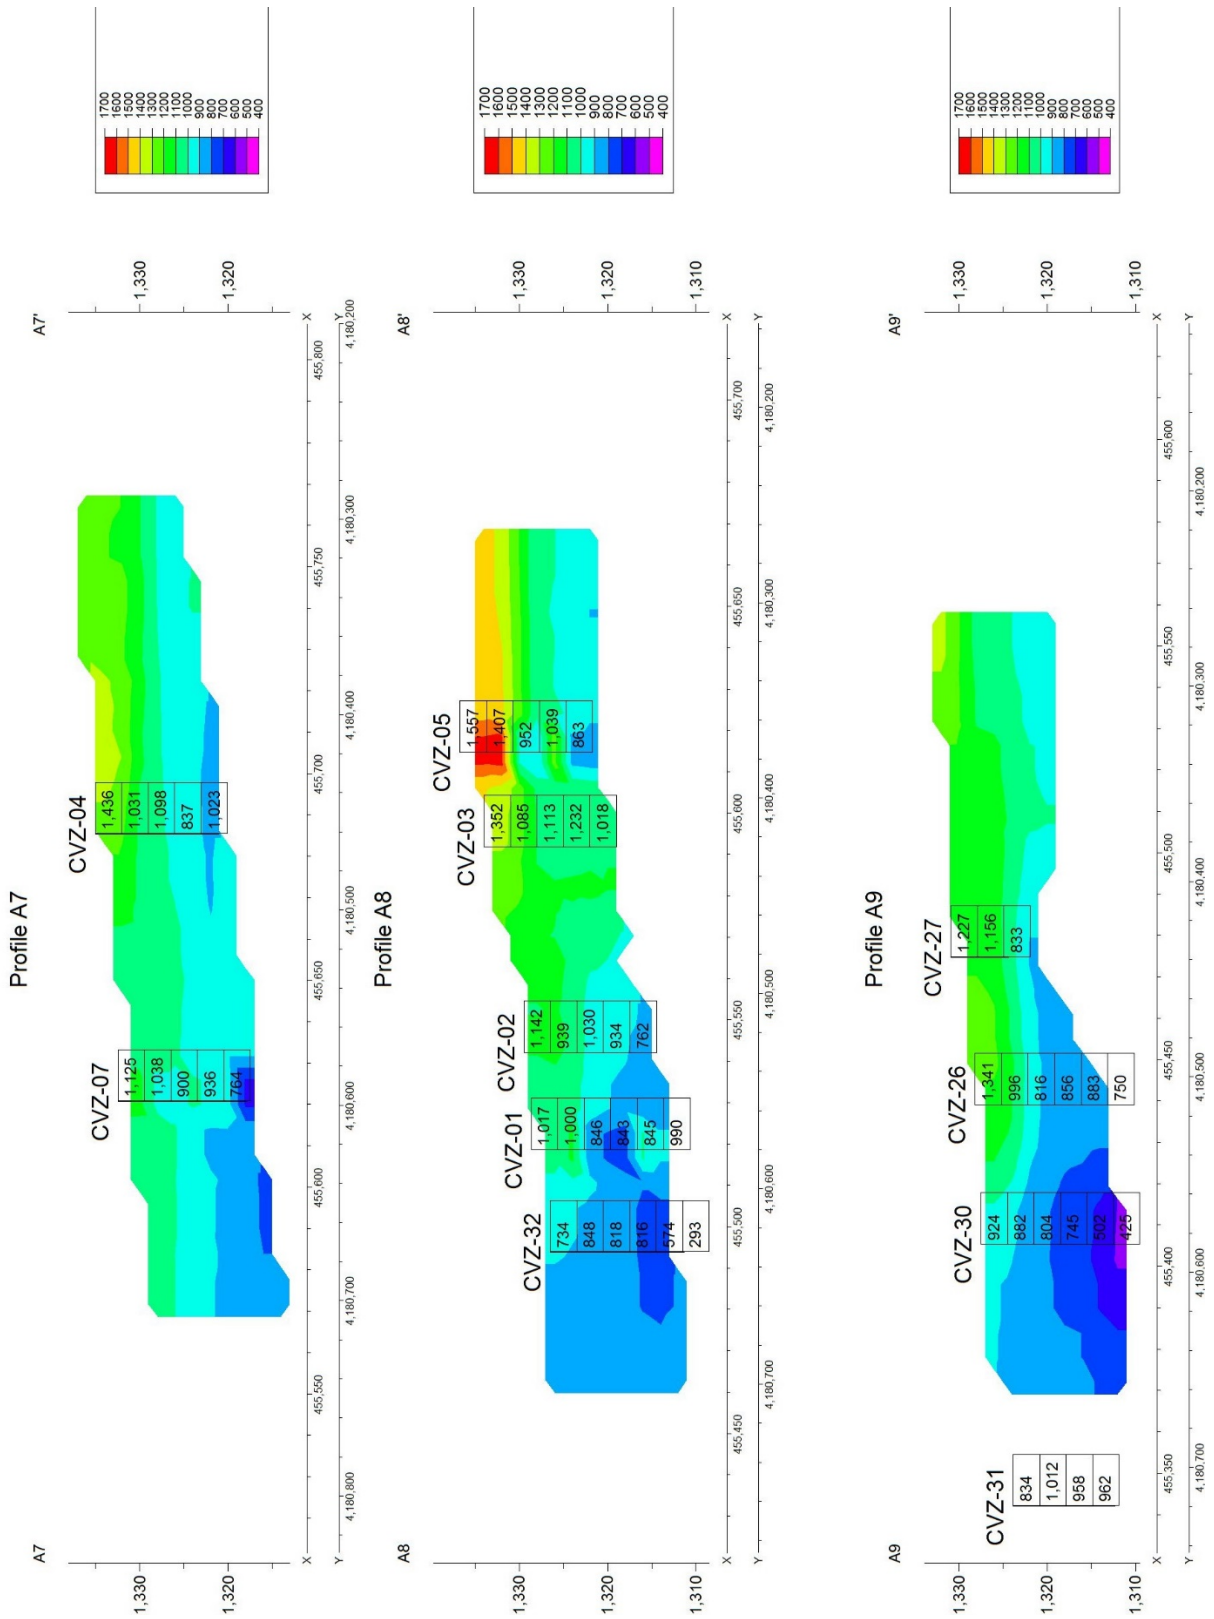


Figure 26 - Profiles A7-A9 through inverse distance model. Vertical exaggeration = 5X.

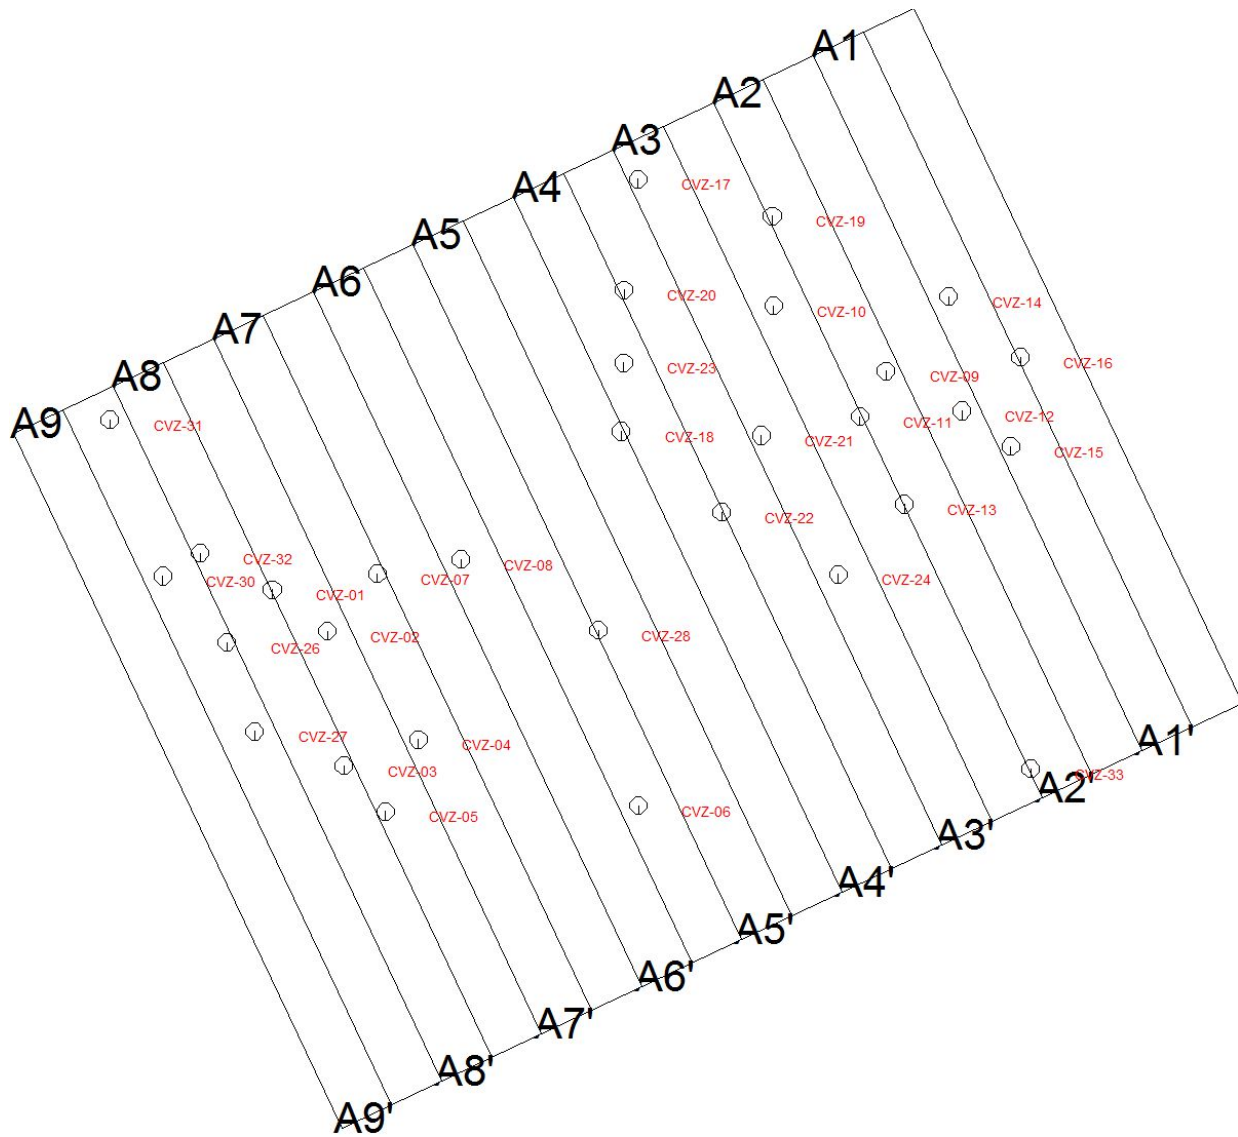


Figure 27 - Locations of Profiles A1-A9.

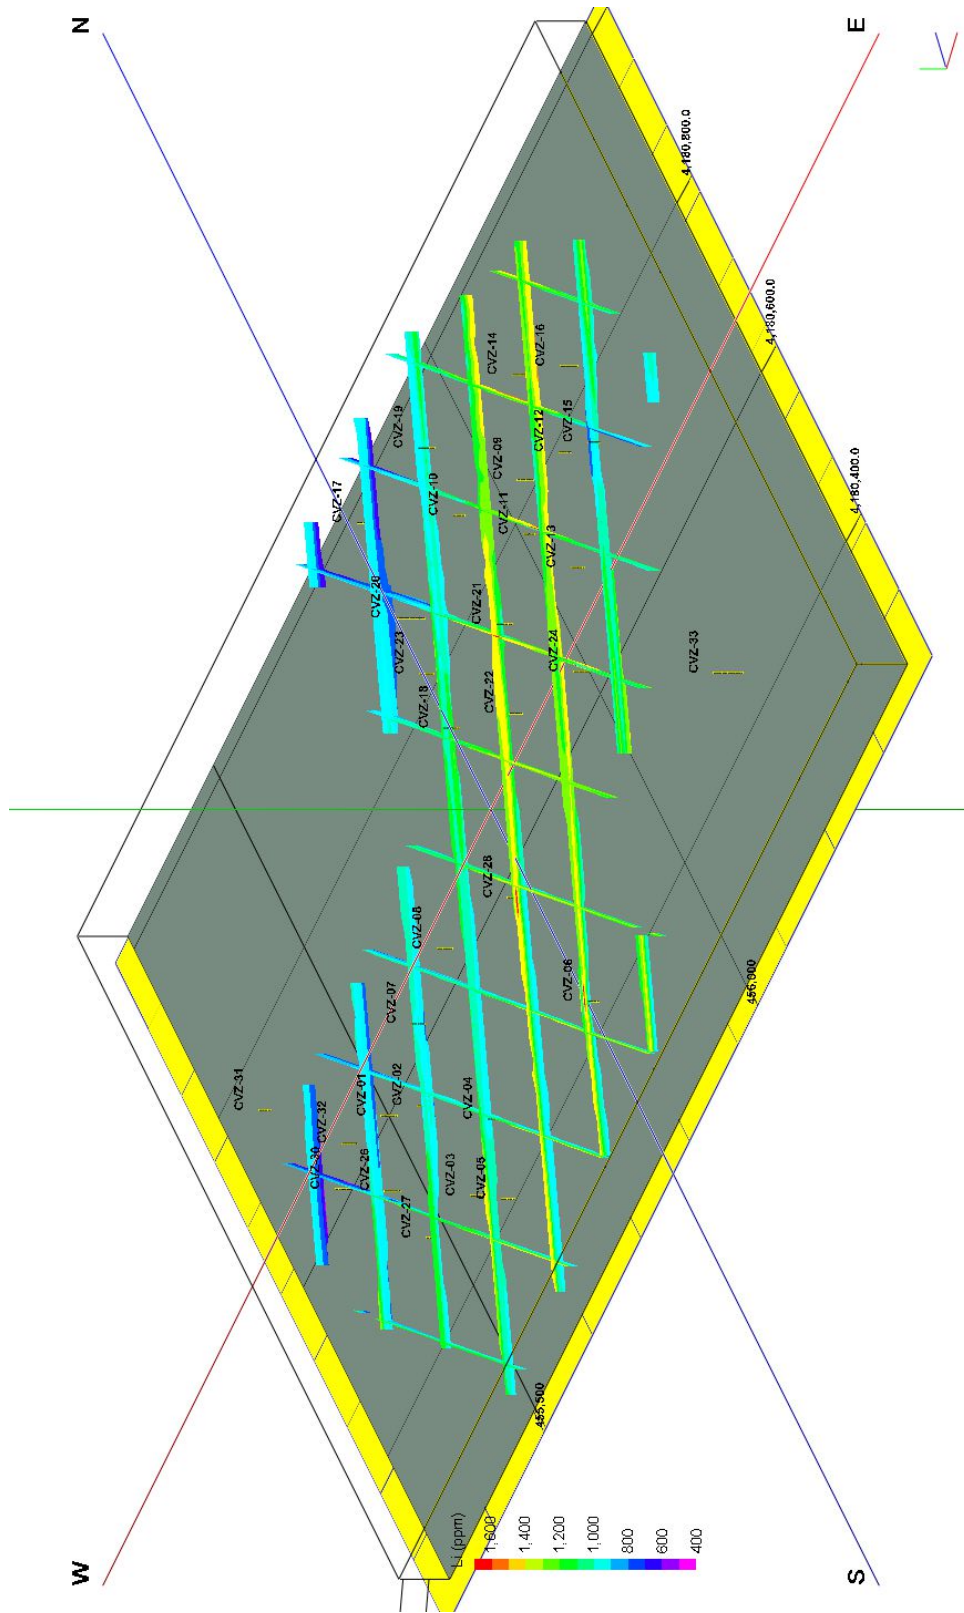


Figure 28 – Fence diagram through the inverse distance model.

The inverse distance model was constructed using voxels with dimensions of 20m X 20m horizontally by 2m vertically, reflecting the relatively thin vertical component of the deposit. A mining bench height for such a deposit has not been developed at this point. Due to the relative simplicity of the deposit, not being complicated by structure or nugget effect, the model chosen was deemed to be adequate for the purposes of this Inferred Mineral Resource estimate.

14.6 Density Determination

Density measurements for the deposit were generated by randomly selecting samples from drill holes inside the area of close-spaced drilling with no regard to depth or elevation. They were selected using a random number generator. Since there were no recognizable lithological breaks within the close-spaced drilling, a random sampling was deemed most appropriate.

It was believed that density measurements could not be performed in the usual way since, once the core had been sampled, the remaining mud/clay samples were nearly always represented by small fragments of the unconsolidated material. Therefore, the densities were determined using method OA-GRA08c by ALS Laboratories in Reno, Nevada, USA. The method was applied to pulps from the selected samples. The method is described by ALS thusly:

“This method uses an automated gas displacement pycnometer to determine density by measuring the pressure change of helium within a calibrated volume. The principle of operation is based on Boyle’s Law. The gas pycnometer measures volume of solid particles using gas (Helium) displacement which will penetrate the finest pores. The pressure difference is measured when a known quantity of helium flows from a precisely known reference volume into a sample cell containing the sample material.”

One drawback to this method of density measurement is that the samples were wet when the core was recovered from the drill holes and were dry when they underwent the specific gravity (SG) measurements. Therefore, the density figures used in the model may be on the low side and the actual tonnage of material in the ground may be higher than that reflected in the model calculations.

The ALS Lab method measures specific gravity and has a lower limit of 0.01 and an upper limit of 20. The SG samples exhibited the following statistics:

Table 6 - SG sample statistics.

Population	20
Minimum	2.57
Maximum	2.73
Average	2.66
Median	2.65

A plot of the specific gravity versus the lithium content of the 20 S.G. samples, Figure 28, indicates there is no relationship between the two factors.

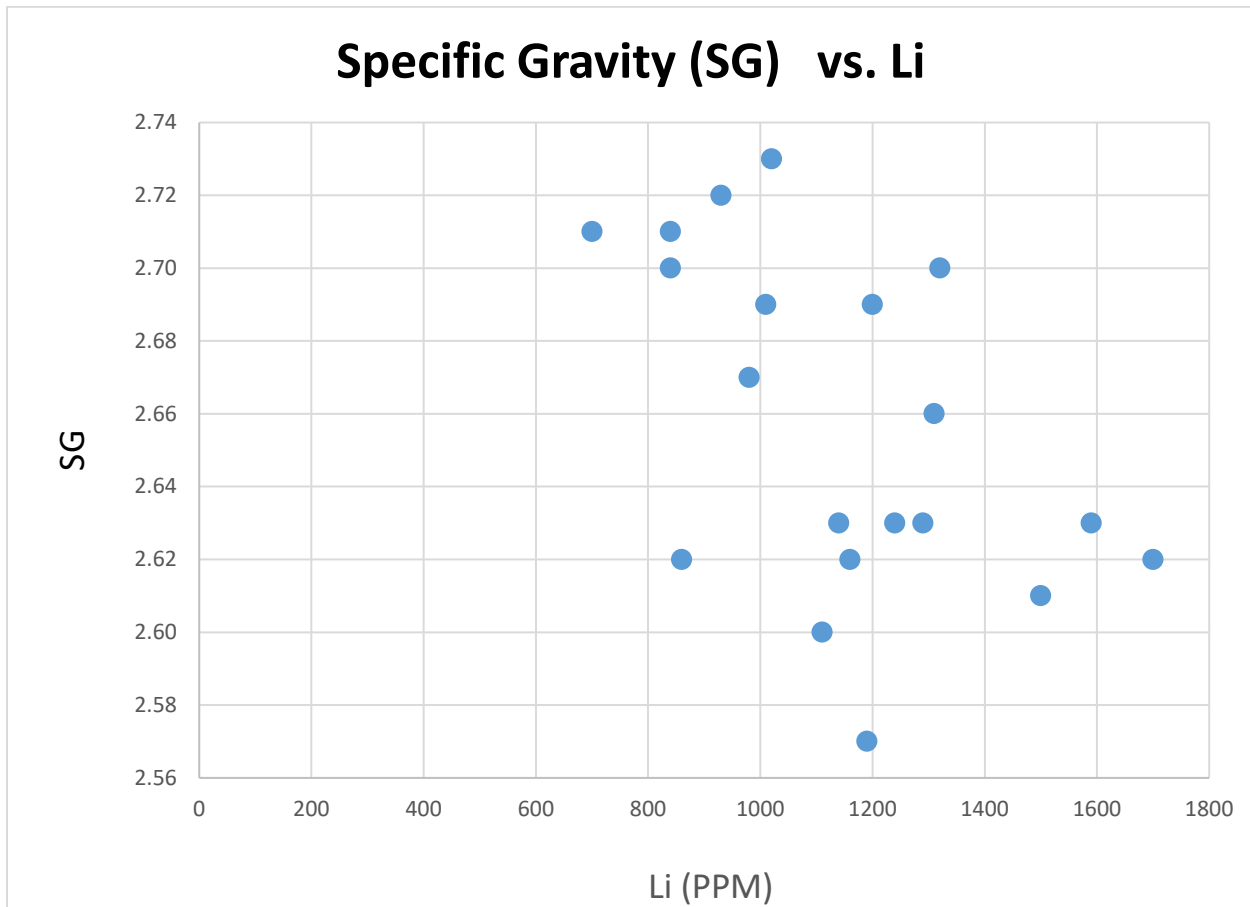


Figure 29 - Relationship between specific gravity and lithium values.

The mean density of 2.66 was used for the tonnage factor in the model calculations.

14.7 Model Results

The reader of this report should be aware that the deposit being defined is for an Inferred Mineral Resource and does not include any other classifications of Mineral Resource or Mineral Reserve. An Inferred Mineral Resource is the lowest level of confidence for mineral resource categories as defined by the Canadian Institute of Mining, Metallurgy and Petroleum (CIM). The CIM definition of an Inferred Mineral Resource includes the statements that, “Geological evidence is sufficient to imply but not verify geological and grade or quality continuity” and “It is reasonably expected that the majority of Inferred Mineral Resources could be upgraded to Indicated Mineral Resources with continued exploration”.

Model calculations were primarily focused on the inverse distance squared method, but as a check, kriging scenarios using various parameters were performed, as well. It was found that the

final kriged tonnages and grades did not vary substantially from the inverse distance squared values. Therefore, inverse distance squared was used for final calculations.

Table 7 is a compilation of the various 2-meter levels of the model segregated into the 200 ppm lithium ranges, showing the relationship between horizontal level and lithium concentration.

Table 8 lists the final tonnage and grade of the entire Inferred Mineral Resource deposit. The result of approximately 17 million tonnes at a grade of 1060 ppm Li is considered to be a reasonable estimate for the deposit, having been checked using several computer-generated and manual methods.

Table 7 - Inverse distance calculated values for each level and Li (ppm) grade range.

Max Elev (m)	Min Elev (m)	Item	454-600 Li (ppm)	600-800 Li (ppm)	800-1000 Li (ppm)	1000-1200 Li (ppm)	1200-1400 Li (ppm)	1400-1600 Li (ppm)	Total Vol (m ³)	Total Mass (kg)
1348	1346	Volume (m ³)	0	0	0	0	0	0	0	
		Mass (kg)	0	0	0	0	0	0		0
		Average (ppm)								
1346	1344	Volume (m ³)	0	0	0	0	0	0	0	
		Mass (kg)	0	0	0	0	0	0		0
		Average (ppm)								
1344	1342	Volume (m ³)	0	0	0	0	0	0	0	
		Mass (kg)	0	0	0	0	0	0		0
		Average (ppm)								
1342	1340	Volume (m ³)	0	800	24800	0	0	0	25600	
		Mass (kg)	0	2128000	65968000	0	0	0		68096000
		Average (ppm)		780	882					
1340	1338	Volume (m ³)	0	800	76000	52000	0	0	128800	
		Mass (kg)	0	2128000	202160000	138320000	0	0		342608000
		Average (ppm)		780	910	1051				
1338	1336	Volume (m ³)	0	0	55200	124800	49600	800	230400	
		Mass (kg)	0	0	146832000	331968000	131936000	2128000		612864000
		Average (ppm)			926	1105	1244	1400		
1336	1334	Volume (m ³)	0	0	11200	205600	120800	2400	340000	
		Mass (kg)	0	0	29792000	546896000	321328000	6384000		904400000
		Average (ppm)			960	1116	1244	1435		
1334	1332	Volume (m ³)	0	0	25600	214400	172800	12800	425600	
		Mass (kg)	0	0	68096000	570304000	459648000	34048000		1132096000
		Average (ppm)			974	1112	1269	1432		
1332	1330	Volume (m ³)	0	0	65600	184000	250400	19200	519200	
		Mass (kg)	0	0	174496000	489440000	666064000	51072000		1381072000
		Average (ppm)			974	1097	1287	1445		
1330	1328	Volume (m ³)	0	0	125600	243200	228800	43200	640800	
		Mass (kg)	0	0	334096000	646912000	608608000	114912000		1704528000
		Average (ppm)			959	1099	1296	1431		
1328	1326	Volume (m ³)	0	0	128800	285600	216000	38400	668800	
		Mass (kg)	0	0	342608000	759696000	574560000	102144000		1779008000
		Average (ppm)			933	1101	1298	1443		
1326	1324	Volume (m ³)	0	800	100800	392800	121600	36000	652000	
		Mass (kg)	0	2128000	268128000	1044848000	323456000	95760000		1734320000
		Average (ppm)		640	898	1089	1261	1482		
1324	1322	Volume (m ³)	0	0	120800	380800	48800	6400	556800	
		Mass (kg)	0	0	321328000	1012928000	129808000	17024000		1481088000
		Average (ppm)			931	1083	1268	1444		
1322	1320	Volume (m ³)	0	1600	198400	322400	23200	0	545600	
		Mass (kg)	0	4256000	527744000	857584000	61712000	0		1451296000
		Average (ppm)		660	935	1088	1224			
1320	1318	Volume (m ³)	0	47200	238400	200800	1600	0	488000	
		Mass (kg)	0	125552000	634144000	534128000	4256000	0		1298080000
		Average (ppm)		747	924	1059	1240			
1318	1316	Volume (m ³)	800	52800	337600	28000	800	0	420000	
		Mass (kg)	2128000	140448000	898016000	74480000	2128000	0		1117200000
		Average (ppm)	600	697	906	1043	1280			
1316	1314	Volume (m ³)	0	47200	239200	25600	0	0	312000	
		Mass (kg)	0	125552000	636272000	68096000	0	0		829920000
		Average (ppm)		698	883	1047				
1314	1312	Volume (m ³)	0	55200	141600	800	0	0	197600	
		Mass (kg)	0	146832000	376656000	2128000	0	0		525616000
		Average (ppm)		765	864	1023				
1312	1310	Volume (m ³)	0	68000	68800	800	0	0	137600	
		Mass (kg)	0	180880000	183008000	2128000	0	0		366016000
		Average (ppm)		770	834	1010				
1310	1308	Volume (m ³)	800	48800	44800	800	0	0	95200	
		Mass (kg)	2128000	129808000	119168000	2128000	0	0		253232000
		Average (ppm)	500	751	831	1050				
1308	1306	Volume (m ³)	4000	21600	15200	0	0	0	40800	
		Mass (kg)	10640000	57456000	40432000	0	0	0		108528000
		Average (ppm)	541	710	844					

Table 8 - Inferred Mineral Resource final numbers.

<i>Li Range (ppm)</i>	<i>All Ranges</i>
Total Mass (Tonnes)	17,098,480
Weighted Avg. Li (ppm)	1060
Weighted Avg. Li %	0.106
Tonnes Li	18,124
Tonnes Li₂CO₃ (LCE)	96,476

23 Adjacent Properties

The perimeter of Noram's claims are located within 1 mile (1.6 kilometers) of Albemarle's lithium brine operations. It is a matter of public record that lithium at Albemarle's plant is produced from deep wells that pump brines from the basin beneath the Clayton Valley playa (Kunasz, 1970; Zampirro, 2005 and Munk, 2011).

Between Albemarle's operation and Noram's land position lies Pure Energy Minerals' Clayton Valley South project where Pure Energy has announced in an NI 43-101 report an inferred resource of 218,000 metric tonnes of lithium carbonate equivalent (LCE) above a cutoff of 20 mg/l (Blois et al, 2017). Pure Energy has subsequently (June 26, 2017) announced a Preliminary Economic Assessment (PEA) showing an expected 20-year project life with a Net Present Value of US\$264 million (after tax at 8% discount rate) and an estimated Internal Rate of Return of 21% (after tax). The Pure Energy resource occurs as basinal brines similar to those at Albemarle's project, has not been verified by the author, and is not necessarily indicative of the mineralization that is the subject of this technical report.

There is potential that wells, if drilled on Noram properties, could penetrate basinal brines like those used by Albemarle to produce lithium and similar to those announced by Pure Energy for their resource estimate and PEA. However, at present it is unknown whether the brines are present beneath Noram claims or whether lithium could be produced economically if the brines are present.

East of Pure Energy's claims and adjacent to the west of Noram's holdings, Cypress Development has recently completed a 9-hole core drilling program of the lithium-rich sediments. Cypress Development's news releases indicated that they had drill intercepts of greater than 200 feet (61 meters) averaging greater than 1000 ppm. The reported results are very similar in geology and lithium grade to those reported herein, however the mineralization discovered by Cypress is not necessarily indicative of mineralization that may be found beneath the property that is the subject of this report.

24 Other Relevant Data and Information

Because of the desert conditions in the Clayton Valley area, water is of major importance to any potential mining operation. In this regard, a scoping study (Hamilton, 2016) was commissioned with Star Point Enterprises, Inc. of Moab, Utah. Star Point's report has indicated that obtaining water rights for the proposed operation could be an involved and somewhat costly undertaking, since the Clayton Valley Basin is over-appropriated (current water rights are in excess of water volumes available for an average year). The report concludes:

“Project water is available in the area for exploration and development primarily through the purchase of water rights from other mining entities within the Clayton Valley groundwater basin. Once quantities for exploration and development are determined, quick research can reveal the likely path towards water delivery. Initial research has revealed that water right purchases in this basin will be in excess of \$900/acre-foot annually as a direct result of large mining operations presently holding the majority of the limited Clayton Valley Basin water resources.”

Having said that, indications from the test work performed by MDS for the extraction of lithium from the sediments are that the process will be able to recycle 77.7% of the process water (See Section 13). The 77.7% figure is a preliminary number and additional testing is required to determine the amount that can finally be recycled.

25 Interpretation and Conclusions

The drilling of 46 shallow core holes into the lithium-rich sediments that were previously identified through surface sampling has provided a basis for the definition of an Inferred Lithium Resource. The lithium assays from the drilling provided results that were quite consistent over a reasonably large area of close-spaced drill holes. The model generated for the Inferred Mineral Resource estimate indicates a zone of higher lithium grades trending northwest-southeast through the area of the resource. The deposit remains open in all directions and at depth and the drilling only tested a very small portion of the area covered by the extensive claim holdings. There is considerable upside potential for increasing the size of the deposit. However, such potential is conceptual in nature. There has been insufficient exploration beyond the modeled deposit and it is uncertain if further exploration will result in an enlargement of the deposit.

Within the model that was generated from the close-spaced drilling was very homogeneous. The model herein reports an Inferred Mineral Resource of approximately 17 million metric tonnes at a grade of about 1060 ppm Li, or 96,476 LCEs. Preliminary economic indicators are that the deposit may be economically extractable at some point. The level of confidence, i.e., the category, of a resource estimate may change with additional exploratory work, such as sampling, drilling, etc.

The success of this sediment mining scenario depends on whether an efficient method of lithium extraction can be found. Should it be shown by the current and future drilling programs that the lithium grades discussed above (and present in the metallurgical samples which yielded

promising results) are continuous over mineable distances, the greatest challenge, and risk, to the project's economic viability will be the development of an economic lithium extraction process. Noram has taken the initial step and has submitted samples of the sediments to MDS for metallurgical testing with positive, although preliminary, results.

25 Recommendations

Noram Ventures and Alba Minerals have successfully completed the early phases of exploration for sediment hosted lithium mineralization, including completing a shallow drilling program on the most promising of its claims. The data obtained from the drilling has been sufficient to generate an Inferred Mineral Resource estimate to move the project forward.

The primary recommendation of this report is to follow the Phase 1 drilling program with a second round (Phase 2) of exploratory drilling adjacent to the presently defined Inferred Mineral Resource area. It is believed that the infill drilling of 12 holes will add significantly to the Inferred Mineral Resource. However, such potential is conceptual in nature. There has been insufficient exploration beyond the modeled deposit and it is uncertain if further exploration will result in an enlargement of the deposit.

Drilling of four additional core holes each in the Zeus XT and Hades claims areas is also recommended. It is anticipated that the additional holes can utilize the existing Notice of Intent with the BLM with minor changes. Some surface sampling of the rounded hills accompanied by a drone topographic survey in the resource area may also add to the Inferred Mineral Resource. The estimated budget to accomplish this is presented in Table 10 below, and is the first part of the spending recommended in this report.

Table 9 – Recommended 2nd Phase – Drilling budget.

Item			Total
Drill 20 shallow core holes to depths of approximately 15m (50ft) + geological logging and sampling of core, surface sampling.			US\$63,000
Assays of core samples	250 samples	\$40/sample	US\$10,000
Assays of surface samples	50samples	\$40/sample	US\$ 2,000
Geological evaluation of drilling results, resource estimation and report writing			US\$15,000
Total			US\$90,000

Noram has begun the process to determine whether the lithium-rich sediments can be processed economically to extract lithium for sale on the open market. The initial testing by MDS was successful in that it showed that extraction of the lithium is possible with an acid leach and membrane technology.

As the second recommended phase of work on the Noram properties, which is not contingent on the results of the drilling recommended above and should be ongoing during the Phase 2 drilling,

it is suggested that the property owners continue to pursue the testing of extraction methods with a pilot-scale test to prove the economic viability of the lithium extraction process, budgeting US\$480,000 for this purpose.

26 References

Aiken, Stephen R., Gowans, Richard, Hawton, Kevin E., Jacobs, Christopher, Ing, Eur, Pilcher, Bruce, Spooner, Jane and Trueman, David L., 2016, NI 43-101 Technical Report on the Preliminary Economic Assessment of Lithium Hydroxide Production, Separation Rapids Lithium Project, Kenora, Ontario, 262 p.

Albers, John P. and Stewart, John H., 1972, Geology and Mineral Deposits of Esmeralda County, Nevada: Nevada Bureau of Mines and Geology Bulletin 78, 80 p.

Albers, John P. and Stewart, John H., 1965, Preliminary Geologic Map of Esmeralda County, Nevada: U. S. Geol. Surv. Field Studies Map MF-298.

Blois, Michael D.S., Weber, Daniel S., Burga, Ernie and Sawyer, Valerie, 2017, Preliminary Economic Assessment of the Clayton Valley Lithium Project, Esmeralda County, Nevada. Technical Report for NI 43-101, Prepared on Behalf of Pure Energy Minerals Ltd.

Baron, Janet, 2017, Summary of Process Bench Testing Reports by MDS: Confidential internal report by AuTec Innovative Extractive Solutions.

Bradley, Dwight, Munk, LeeAnn, Jochens, Hillary, Hynek, Scott, and Labay, Keith, 2013, A preliminary deposit model for lithium brines: U.S. Geological Survey Open-File Report 2013–1006, 6 p.

Burga, Ernest, Burga, David, Rosko, Mike, King, Mark, Abbey, Daron and Sanford, Tony, 2017, NI 43 –101 Technical Report, Updated Feasibility Study, Reserve Estimation and Lithium Carbonate Production at the Cauchari-Olaroz Salars, Jujuy Province, Argentina, 318 p.

Davis, J. R., 1981, Late Cenozoic Geology of Clayton Valley, Nevada and the Genesis of a Lithium-Enriched Brine: Ph.D. Dissertation, University of Texas, Austin, 249p.

Davis, J. R. and Vine, J. D., 1979, Stratigraphic and Tectonic Setting of the Lithium Brine Field, Clayton Valley, Nevada: RMAG-UGA 1979 Basin and Range Symposium, pp. 421-430.

Foy, Travis A., 2011, Quaternary Faulting in Clayton Valley, Nevada: Implications for Distributed Deformation in the Eastern California Shear Zone – Walker Lane: Georgia Institute of Technology Master's Thesis.

Hamilton, Don, 2016, Scoping Study, Water for Exploration and Development within the Clayton Valley Basin: Internal Noram Ventures company report.

Kunasz, Ihor A., 1970, Geology and Geochemistry of the Lithium Deposit in Clayton Valley, Esmeralda County, Nevada: University of Pennsylvania PhD Thesis.

Kunasz, Ihor A., 1974, Lithium Occurrence in the Brines of Clayton Valley, Esmeralda County, Nevada: Fourth Symposium on Salt – Northern Ohio Geological Society, pp. 57-66.

Lein, Larry, 2016, MDS Bench Report – Lithium Bearing Clays Leached with Acid, Processed with MDS proprietary membrane process: Confidential internal report by Membrane Development Technologies LLC.

Lein, Larry, 2017, Process Bench Testing Report, Lithium Bearing Samples for Noram Ventures, Inc.: Confidential internal report by Membrane Development Technologies LLC.

Munk, LeeAnn and Chamberlain, C. Page, 2011, Final Technical Report: G10AP00056 – Lithium Brine Resources: A Predictive Exploration Model: USGS Mineral Resources External Research Program.

Zampirro, Danny, 2005, Hydrogeology of Clayton Valley Brine Deposits, Esmeralda County, Nevada: The Professional Geologist, Vol. 42, No. 3, pp. 46-54.

Certificate of the Author

I, Bradley C. Peek, MSc., CPG do hereby certify that:

1. I am currently employed as a Consulting Geologist at 438 Stage Coach Lane, New Castle, Colorado 81647, USA
2. This certificate applies to the Technical Report titled “Technical Report, Lithium Inferred Mineral Resource Estimate, Clayton Valley, Esmeralda County, Nevada, USA” with the effective date July 24, 2017 (the “Technical Report”).
3. I graduated in 1970 from the University of Nebraska with Bachelor of Science degree in Geology and in 1975 from the University of Alaska with Master of Science degree in Geology.
4. I am a member in good standing with the Society of Economic Geologists and the American Institute of Professional Geologists (Certified Professional Geologist #11299).
5. I have continuously practiced my profession for 45 years in the areas of mineral exploration and geology. I have explored for copper, lead, zinc, silver and gold in 10 states of the USA and 8 foreign countries. I have spent most of 2016 and 2017 exploring for lithium deposits in the Clayton Valley, Nevada, USA. I have more than 5 years’ experience generating open pit resource estimates for approximately 18 mineral deposits, primarily for gold and base metals using GEMCOM software.
6. I visited the Noram Ventures Clayton Valley Lithium property on May 5 – 7, 2016, July 21 – 25, 2016, August 3 – 6, 2016, December 12 – 22, 2016, and January 8 – 27, 2017
7. I supervised the preparation of the report entitled “Technical Report, Lithium Inferred Mineral Resource Estimate, Clayton Valley, Esmeralda County, Nevada, USA” with the effective date July 24, 2017, including the conclusions reached and the recommendations made, with the exception of those portions indicated under the heading, “Reliance on Other Experts”.
8. I am independent of Alba Minerals Ltd. and Noram Ventures Inc. applying all of the tests in Section 5.1.1, Part 1.5 of NI 43-101.
9. I have had no prior involvement with the property that is the subject of the Technical Report other than that which is stated in this report and previous Noram and Alba NI 43-101 reports.
10. I have read the definition of “qualified person” set out in National Instrument 43-101 (NI 43-101) and certify that by reason of my education, professional affiliation, and past relevant work experience, I fulfil the requirement to be an independent qualified person for the purposes of this NI 43-101.
11. As of the effective date of the Technical Report, to the best of my knowledge, information and belief, this Technical Report contains all of the scientific and technical information that is required to be disclosed to make the Technical Report not misleading.
12. I consent to the filing of the Technical Report with any stock exchange and other regulatory authority and any publication by them of the Technical Report for regulatory purposes, including electronic publication in the public company files on their websites accessible by the public.

Dated October 27, 2017




Bradley C. Peek, CPG

Date and Signature Page

The report herein, entitled “Lithium Inferred Mineral Resource Estimate, Clayton Valley, Esmeralda County, Nevada, USA” has an effective date of July 24, 2017.



Bradley C. Peek, MSc., CPG

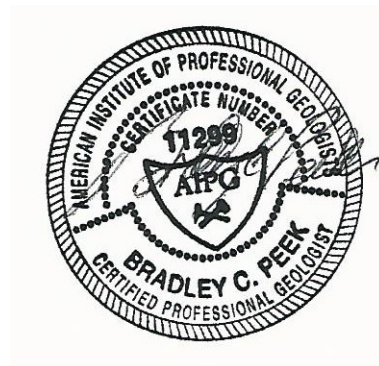

RAYMOND P. SPANJERS, MS, P.Geo
CONSULTING GEOLOGIST
891 Ridge Vista Road, Box 85
Gerton, NC 28735
Telephone: 229-254-7855 Email: rayspanjers@gmail.com

CERTIFICATE of AUTHOR

I, Raymond P. Spanjers do hereby certify that:

1. I am currently engaged as a Geological Consultant.
2. I am a graduate of the University of Wisconsin – Parkside with a Bachelor of Science in Earth Science (1977), and a Master of Science degree in Geology from North Carolina State University (1983).
3. I am a Registered Professional Geologist through the Society for Mining, Metallurgy & Exploration (SME), Number 3041730RM.
4. I have practiced by profession in geology since 1980 and have 37 years of experience in mineral exploration, mining and mineral processing of industrial minerals, which include spodumene, and lithium brines, quartz, feldspar, mica, olivine, attapulgitic, silica sand and tripoli.
5. My experience includes 3-D modeling of several hard rock igneous and sedimentary ore deposits for a major industrial mineral mining company.
6. I have read the definition of “qualified person” set out in NI 43-101 (“NI 43-101”) and certify that by reason of my education, affiliation with a professional association (as defined in NI 43-101) and past relevant work experience, I fulfill the requirements to be a “qualified person” for the purposes of NI 43-101.
7. I am responsible for Section 14 in the NI 43-101 Technical Report “Lithium Inferred Mineral Resource Estimate, Clayton Valley, Esmeralda County, Nevada”.
8. I do not hold, nor do I expect to receive, any securities or any other interest in any corporate entity, private or public, with interests in the properties that are the subject of this report or in the properties relationship with the issuer, nor to the best of my knowledge do I have any interest in any securities of any corporate entity with property within a two (2) kilometer distance of any of the subject properties.
9. I am independent of Noram Ventures Ltd. according to the criteria stated in Section 1.5 of NI 43-101.
10. I have read NI 43-101 and Form NI 43-101F1, and the Technical Report has been prepared in compliance with that instrument and form.



Dated this 27th day of October, 2017.

/s/ Raymond P. Spanjers (Signature)

Signature of Qualified Person

“Raymond P. Spanjers”

Print name of Qualified Person

Consent of Qualified Person:

To: Securities Regulatory Authority

Alberta
British Columbia
Ontario

I, Bradley C. Peek, do hereby consent to the public filing of the technical report entitled "Lithium Inferred Mineral Resource Estimate, Clayton Valley, Esmeralda County, Nevada, USA" with the effective date of 24 July, 2017 (the "Technical Report") by Noram Ventures, Inc. and Alba Minerals Ltd (the "Issuers"), and I acknowledge that the Technical Report will become part of the Issuer's public record. I also consent to the use of extracts from, or a summary of, the technical report.

Signed

A handwritten signature in black ink on a light-colored rectangular background. The signature is cursive and reads "Bradley C. Peek".

Dated

October 27, 2017 .